



Date: August 2021

Profile and anchor equipment: We think holistically.

We offer our customers an integrated range of systems solutions all over the world. Key elements are the sale and hire of steel sheet piling and anchor equipment. As a multi-supplier we provide a broad range of products from various manufacturers, supplemented by a comprehensive service package of consulting, technical support, logistics and leasing.


Contents

Technical handbook

- 02 Hot-rolled sheet pile sections**
 - 02 U-Sections
 - 13 Z-Sections
 - 17 Steel box piles
 - 19 Combined sheet pile walls
 - 24 Cold-rolled sheet piling sections**
 - 24 Trench sheeting
 - 26 Lightweight sections
 - 27 Terms of delivery and steel grades**
 - 28 Interlocks**
 - 28 Corner and junction piles for U- and Z-profiles
 - 30 Corner and junction piles for U- and Z-profiles, traditional
 - 31 Corner and junction piles for U- and Z-profiles, universal
 - 32 Corner and junction piles for cold-rolled sheet piles
 - 33 Sealing systems**
 - 33 thyssenkrupp interlock sealing system
 - 34 Bitumen-based interlock fillers
 - 35 Other sealing methods
 - 35 Criteria for selecting a suitable interlock sealing
 - 36 Spot-on selection
 - 37 Comparison of k-values
 - 38 Anchor equipment**
 - 38 Round steel tie rods
 - 43 thyssenkrupp drilled injection pile system
-


Hot-rolled sheet pile sections

Overview: U-Sections

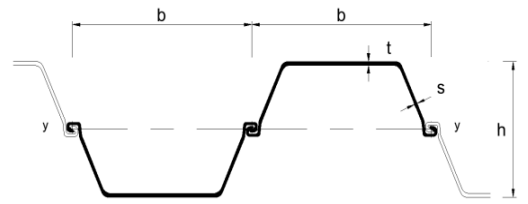

Technical data												
thyssenkrupp Sections	Elastic section modulus W_y cm ³	Plastic section modulus $W_{y,pl}$ cm ³	Weight kg/m ²	Weight Single pile kg/m	Moment of inertia I_y cm ⁴ /m	Flange thickness t mm	Web thickness s mm	Height h mm	Section width b mm	Classification to DIN EN 1993-5		
										S 270 GP	S 355 GP	S 430 GP
tkL 601	744	895	77.2	46.3	11,530	7.5	6.4	310.0	600	2	3	3
tkL 601 FP	745	906	79.0	47.4	11,547	7.2	7.0	310.0	600	3	3	3
tkL 601 K	775	936	80.8	48.5	12,019	7.8	6.8	310.0	600	2	3	3
tkL 602 A	806	979	85.5	51.3	12,499	8.0	7.3	310.0	600	2	3	3
tkL 602	842	1022	89.0	53.4	13,046	8.4	7.6	310.0	600	2	3	3
tkL 602 K	877	1,065	92.3	55.4	13,590	8.8	7.9	310.0	600	2	2	3
tkL 603 A	1,138	1,316	102.5	61.5	18,205	9.0	8.0	320.0	600	3	4	4
tkL 603	1,200	1,386	107.0	64.2	19,199	9.6	8.2	320.0	600	3	3	4
tkL 603 KN	1,230	1,427	111.5	66.9	19,682	9.8	8.6	320.0	600	3	3	4
tkL 603 K	1,241	1,444	113.0	67.8	19,853	9.8	9.0	320.0	600	3	3	4
tkL 603 Z	1,300	1,525	120.2	72.1	20,930	10.0	10.0	322.0	600	3	3	4
tkL 603 Z11	1,404	1,653	131.0	78.6	22,470	11.0	11.0	320.0	600	2	3	3
tkL 604 A	1,564	1,823	118.3	71.0	30,495	9.6	8.8	390.0	600	3	3	4
tkL 604	1,618	1,885	121.8	73.1	31,548	10.0	9.0	390.0	600	3	3	4
tkL 604 K	1,672	1,947	125.3	75.2	32,600	10.4	9.2	390.0	600	3	3	3
tkL 605 A	1,821	2,125	127.5	76.5	38,243	10.7	9.0	420.0	600	2	3	3
tkL 605 N	2,019	2,348	136.9	82.1	42,664	12.0	9.5	422.6	600	2	2	3
tkL 605 KN	2,117	2,466	142.7	85.6	44,886	12.6	10.0	424.0	600	2	2	3
tkL 606 A	2,205	2,541	142.3	85.4	47,402	13.4	9.0	430.0	600	2	2	2
tkL 606 AN	2,355	2,714	149.6	89.8	50,878	14.4	9.4	432.0	600	2	2	2
tkL 606 N	2,506	2,887	156.8	94.1	54,389	15.4	9.8	434.0	600	2	2	2
tkL 628 -1,5	2,607	3,006	158.6	95.2	58,938	14.8	9.5	452.1	600	2	2	2
tkL 628 AN	2,701	3,114	163.1	97.9	61,219	15.4	9.8	453.3	600	2	2	2
tkL 628 A	2,809	3,238	168.0	100.8	63,856	16.1	10.0	454.7	600	2	2	2
tkL 628	2,841	3,276	169.6	101.8	64,640	16.3	10.1	455.1	600	2	2	2
tkL 628 K	2,903	3,347	172.5	103.5	66,165	16.7	10.3	455.9	600	2	2	2
tkL 607 A	3,006	3,460	177.1	106.2	68,232	17.7	10.0	453.9	600	2	2	2
tkL 607	3,211	3,701	187.3	112.4	73,300	19.0	10.6	456.5	600	2	2	2
tkL 607 K	3,365	3,882	194.7	116.8	77,153	20.0	11.0	458.5	600	2	2	2

Overview: Special sections*

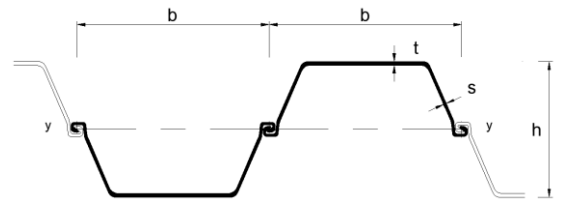

Technical data													
thyssenkrupp Sections	Elastic section modulus W_y cm ³	Plastic section modulus $W_{y,pl}$ cm ³	Weight kg/m ²	Weight Single pile kg/m	Moment of inertia I_y cm ⁴ /m	Flange thickness t mm	Web thickness s mm	Height h mm	Section width b mm	Classification to DIN EN 1993-5			
										S 270 GP	S 355 GP	S 430 GP	
tkL 602 A8	831	1,016	89.5	53.7	12,843	8.0	8.0	309.2	600	2	3	3	
tkL 602 90	854	1,038	90.0	54.0	13,241	8.5	7.7	310.2	600	2	2	3	
tkL 602 D	881	1,071	92.9	55.7	13,650	8.8	8.0	310.0	600	2	2	3	
tkL 602 +0,5	894	1,087	93.3	56.0	13,905	8.9	8.1	311.0	600	2	2	3	
tkL 602 +0,7	907	1,101	94.0	56.4	14,128	9.1	8.1	311.4	600	2	2	3	
tkL 603 AN	1,161	1,342	104.0	62.4	18,601	9.2	8.1	320.4	600	3	4	4	
tkL 603 108	1,215	1,404	108.0	64.8	19,456	9.7	8.3	320.2	600	3	3	4	
tkL 603 K10	1,261	1,465	114.1	68.4	20,196	10.0	9.0	320.4	600	3	3	4	
tkL 604 AN	1,409	1,637	107.1	64.3	27,478	8.7	7.7	390.0	600	3	4	4	
tkL 604 124	1,659	1,932	124.0	74.4	32,407	10.3	9.1	390.6	600	3	3	3	
tkL 605 A +0,5	1,885	2,194	130.1	78.1	39,681	11.2	9.0	421.0	600	2	3	3	
tkL 605 N 1975	1,975	2,299	134.8	80.9	41,681	11.7	9.4	422.0	600	2	3	3	
tkL 605 N 2020	2,020	2,350	137.0	82.2	42,684	12.0	9.5	422.6	600	2	2	3	
tkL 605 N 138,5	2,050	2,384	138.5	83.1	43,362	12.2	9.6	423.0	600	2	2	3	
tkL 605 N 139,2	2,065	2,401	139.2	83.5	43,699	12.3	9.6	423.2	600	2	2	3	
tkL 605 K	2,068	2,414	142.9	85.7	43,434	12.4	10.0	420.0	600	2	2	3	
tkL 605 N +0,5	2,094	2,433	140.5	84.3	44,350	12.5	9.7	423.6	600	2	2	3	
tkL 606 AS +0,5	2,228	2,578	144.9	87.0	47,898	13.4	9.5	430.0	600	2	2	2	
tkL 606 A +0,5	2,269	2,611	144.9	86.9	48,893	13.9	9.0	431.0	600	2	2	2	
tkL 606 AN 10	2,402	2,778	153.4	92.0	51,913	14.5	10.0	432.2	600	2	2	2	
tkL 606 N 157	2,517	2,897	157.0	94.3	54,645	15.5	9.8	434.2	600	2	2	2	
tkL 504 A	1,423	1,677	127.0	63.5	24,198	11.2	8.7	340.0	500	2	2	2	
tkL 504	1,504	1,771	133.2	66.6	25,575	12.0	9.0	340.0	500	2	2	2	
tkL 504 K	1,602	1,885	140.6	70.3	27,233	13.0	9.3	340.0	500	2	2	2	
tkL 507 A	2,800	3,275	184.6	92.3	61,185	17.5	10.2	437.0	500	2	2	2	
tkL III n	1,600	1,857	155.5	62.2	23,206	13.0	9.0	290.0	400	2	2	2	

*Only on request

Details: U-Sections

Section

S = Single pile

D = Double pile

T = Triple pile

Technical data		Elastic section modulus W_y cm ³	Weight kg/m	Cross sectional area cm ²	Coating area m ² /m	Static moment S_y cm ³	Moment of inertia I_y cm ⁴	Radius of gyration cm	
thyssenkrupp Sections tkL 601 		per m wall	744	77.2	98.3	2.47	448	11,530	10.83
		per S	221	46.3	59.0	1.60	2,360	6.32	
		per D	893	92.6	118.0	3.08	13,836	10.83	
		per T	1,044	138.9	177.0	4.56	19,235	10.42	
tkL 601 FP 		per m wall	745	79.0	100.7	2.47	453	11,547	10.70
		per S	223	47.4	60.4	1.60	2,360	6.25	
		per D	894	94.8	120.8	3.08	13,857	10.70	
		per T	1,047	142.3	181.2	4.56	19,262	10.30	
tkL 601 K 		per m wall	775	80.8	102.9	2.47	468	12,019	10.81
		per S	229	48.5	61.8	1.60	2,457	6.31	
		per D	931	97.0	123.5	3.08	14,423	10.81	
		per T	1,088	145.5	185.3	4.56	20,050	10.40	
tkL 602 A 		per m wall	806	85.5	109.0	2.47	490	12,499	10.71
		per S	245	51.3	65.4	1.60	2,601	6.31	
		per D	968	102.6	130.7	3.08	14,998	10.71	
		per T	1,135	153.9	196.1	4.57	20,865	10.31	
tkL 602 		per m wall	842	89.0	113.3	2.47	511	13,046	10.73
		per S	252	53.4	68.0	1.60	2,698	6.30	
		per D	1,010	106.8	136.0	3.08	15,655	10.73	
		per T	1,184	160.2	204.0	4.57	21,773	10.28	
tkL 602 K 		per m wall	877	92.3	117.7	2.47	533	13,590	10.75
		per S	260	55.4	70.6	1.60	2,797	6.29	
		per D	1,052	110.8	141.2	3.08	16,308	10.75	
		per T	1,232	166.2	211.8	4.56	22,676	10.35	

- 1) The elastic section modulus of the U-profiles may only be applied in the static calculation if at least every second interlock is crimped and welded to absorb the shear forces
- 2) Elastic section modulus: for S and T related to the axis of gravity of the respective element, for D and per m wall related to the wall axis y-y

Technical data		Elastic section modulus W_y cm^3	Weight kg/m	Cross sectional area cm^2	Coating area m^2/m	Static moment S_y cm^3	Moment of inertia I_y cm^4	Radius of gyration cm
	per m wall	1,138	102.5	130.6	2.65	658	18,205	11.81
	per S	296	61.5	78.3	1.72		3,503	6.69
	per D	1,365	123.0	156.7	3.31		21,846	11.81
	per T	1,574	184.5	235.0	4.90		30,296	11.35
	per m wall	1,200	107.0	136.3	2.65	693	19,199	11.87
	per S	304	64.2	81.8	1.73		3,641	6.67
	per D	1,440	128.4	163.6	3.31		23,039	11.87
	per T	1,657	192.6	245.3	4.90		31,933	11.41
	per m wall	1,230	111.5	142.0	2.65	713	19,682	11.77
	per S	324	66.9	85.2	1.73		3,856	6.73
	per D	1,476	133.7	170.4	3.32		23,618	11.77
	per T	1,705	200.6	255.6	4.90		32,776	11.32
	per m wall	1,240	113.0	143.9	2.65	722	19,853	11.74
	per S	326	67.8	86.4	1.73		3,873	6.70
	per D	1,489	135.6	172.7	3.32		23,824	11.74
	per T	1,720	203.4	259.1	4.90		33,056	11.30
	per m wall	1,300	120.2	153.1	2.65	763	20,930	11.69
	per S	350	72.1	91.9	1.73		4,162	6.73
	per D	1,560	144.2	183.7	3.32		25,115	11.69
	per T	1,808	216.3	275.6	4.91		34,874	11.25
	per m wall	1,404	131.0	166.9	2.64	827	22,470	11.60
	per S	375	78.6	100.2	1.73		4,472	6.68
	per D	1,685	157.2	200.3	3.32		26,964	11.60
	per T	1,954	235.8	300.5	4.90		37,443	11.16
	per m wall	1,564	111.3	150.8	2.88	912	30,495	14.22
	per S	418	71.0	90.5	1.85		5,834	8.03
	per D	1,877	142.0	181.0	3.58		36,594	14.22
	per T	2,167	213.0	271.5	5.31		50,737	13.67
	per m wall	1,618	121.8	155.2	2.85	943	31,548	14.26
	per S	426	73.1	93.1	1.85		5,984	8.02
	per D	1,941	146.2	186.2	3.56		37,857	14.26
	per T	2,240	219.3	279.4	5.27		52,471	13.70

- 1) The elastic section modulus of the U-profiles may only be applied in the static calculation if at least every second interlock is crimped and welded to absorb the shear forces
- 2) Elastic section modulus: for S and T related to the axis of gravity of the respective element, for D and per m wall related to the wall axis y-y

Technical data

	Elastic section modulus W_y cm^3	Weight kg/m	Cross sectional area cm^2	Coating area m^2/m	Static moment S_y cm^3	Moment of inertia I_y cm^4	Radius of gyration cm	
	per m wall	1,672	125.3	159.7	2.85	974	32,600	14.29
	per S	435	75.2	95.8	1.85		6,140	8.00
	per D	2,006	150.4	191.7	3.56		39,121	14.29
	per T	2,312	225.6	287.5	5.27		54,207	13.73
	per m wall	1,821	127.5	162.5	2.91	1,063	38,243	15.34
	per S	475	76.5	97.5	1.89		7,113	8.54
	per D	2,185	153.0	194.9	3.64		45,892	15.34
	per T	2,517	229.5	292.4	5.39		63,560	14.74
	per m wall	2,019	136.9	174.4	2.90	1,174	42,664	15.64
	per S	486	82.1	104.6	1.88		7,488	8.46
	per D	2,423	164.2	209.2	3.62		51,197	15.64
	per T	2,773	264.4	313.8	5.36		70,759	15.02
	per m wall	2,117	142.7	181.8	2.90	1,233	44,886	15.72
	per S	498	85.6	109.1	1.88		7,742	8.43
	per D	2,541	171.7	218.1	3.62		53,864	15.72
	per T	2,904	256.8	327.1	5.36		74,399	15.08
	per m wall	2,205	142.3	181.3	2.93	1,271	47,402	16.17
	per S	500	85.4	108.8	1.90		7,981	8.56
	per D	2,646	170.8	217.6	3.65		56,883	16.17
	per T	3,011	256.2	326.4	5.41		78,504	15.51
	per m wall	2,355	149.6	190.6	2.92	1,357	50,878	16.33
	per S	512	89.8	114.4	1.89		8,281	8.51
	per D	2,827	179.6	228.8	3.65		61,056	16.33
	per T	3,207	269.5	343.3	5.40		84,168	15.66
	per m wall	2,506	156.8	199.8	2.92	1,443	54,389	16.50
	per S	520	94.1	119.9	1.89		8,545	8.44
	per D	3,008	188.2	239.7	3.65		65,266	16.50
	per T	3,401	282.3	359.6	5.40		89,870	15.81

- 1) The elastic section modulus of the U-profiles may only be applied in the static calculation if at least every second interlock is crimped and welded to absorb the shear forces
- 2) Elastic section modulus: for S and T related to the axis of gravity of the respective element, for D and per m wall related to the wall axis y-y

Technical data		Elastic section modulus W_y cm^3	Weight kg/m	Cross sectional area cm^2	Coating area m^2/m	Static moment S_y cm^3	Moment of inertia I_y cm^4	Radius of gyration cm
	per m wall	2,607	158.6	202.0	2.94	1.503	58,938	17.08
	per S	567	95.2	121.2	1.88		9,560	8.88
	per D	3,129	190.3	242.4	3.66		70,725	17.08
	per T	3,549	285.5	363.6	5.44		97,487	16.37
	per m wall	2,701	163.1	207.8	2.94	1.557	61,219	17.17
	per S	575	97.9	124.7	1.88		9,763	8.85
	per D	3,241	195.7	249.3	3.66		73,462	17.17
	per T	3,671	293.6	374.0	5.44		101,204	16.45
	per m wall	2,809	168.0	214.0	2.94	1.619	63,856	17.27
	per S	582	100.0	128.4	1.88		9,973	8.81
	per D	3,370	201.6	256.8	3.66		76,627	17.29
	per T	3,810	302.4	385.2	5.44		105,494	16.55
	per m wall	2,841	169.6	216.1	2.94	1.638	64,640	17.29
	per S	586	101.8	129.7	1.88		10,053	8.81
	per D	3,409	203.6	259.3	3.66		77,568	17.29
	per T	3,852	305.4	389.0	5.44		106,775	16.57
	per m wall	2,903	172.5	219.8	2.94	1.674	66,165	17.35
	per S	590	103.5	131.9	1.88		10,173	8.78
	per D	3,483	207.0	263.7	3.66		79,398	17.35
	per T	3,932	310.5	395.6	5.44		109,205	16.62
	per m wall	3,006	177.1	225.6	2.98	1.730	68,232	17.39
	per S	586	106.2	135.3	1.95		10,164	8.67
	per D	3,608	212.5	270.7	3.75		81,879	17.39
	per T	4,060	318.7	406.0	5.54		112,560	16.65
	per m wall	3,211	187.3	238.6	2.98	1.851	73,300	17.53
	per S	605	112.4	143.2	1.95		10,617	8.61
	per D	3,854	224.8	286.3	3.75		87,960	17.53
	per T	4,328	337.1	429.5	5.54		120,819	16.77
	per m wall	3,365	194.7	248.0	2.98	1.941	77,153	17.64
	per S	617	116.8	148.8	1.95		10,920	8.57
	per D	4,038	233.6	297.5	3.75		92,583	17.64
	per T	4,528	350.4	446.3	5.54		127,084	16.87

1) The elastic section modulus of the U-profiles may only be applied in the static calculation if at least every second interlock is crimped and welded to absorb the shear forces
 2) Elastic section modulus: for S and T related to the axis of gravity of the respective element, for D and per m wall related to the wall axis y-y

Details: Special sections*

Technical data		Elastic section modulus W_y cm^3	Weight kg/m	Cross sectional area cm^2	Coating area m^2/m	Static moment S_y cm^3	Moment of inertia I_y cm^4	Radius of gyration cm	
	tkL 602A8	per m wall	831	89.5	114.0	2.47	508	12,843	10.61
		per S	252	53.7	68.4	1.60		2,668	6.25
		per D	997	107.4	136.8	3.08		15,411	10.61
		per T	1,170	161.1	205.2	4.56		21,438	10.22
	tkL 602 90	per m wall	854	90.0	114.7	2.47	519	13,241	10.74
		per S	253	54.0	68.8	1.60		2,720	6.29
		per D	1,024	108.1	137.6	3.08		15,890	10.74
		per T	1,200	162.1	206.5	4.57		22,093	10.34
	tkL 602D	per m wall	881	92.9	118.3	2.47	536	13,650	10.74
		per S	260	55.7	71.0	1.60		2,802	6.28
		per D	1,057	111.4	142.0	3.08		16,380	10.74
		per T	1,238	167.2	213.0	4.56		22,774	10.34
	tkL 602 +0,5	per m wall	894	93.3	118.8	2.47	543	13,905	10.82
		per S	257	56.0	71.3	1.60		2,789	6.26
		per D	1,073	112.0	142.6	3.08		16,686	10.82
		per T	1,253	168.0	213.9	4.57		23,178	10.41
	tkL 602 +0,7	per m wall	907	94.0	119.8	2.47	551	14,128	10.86
		per S	259	56.4	71.9	1.60		2,819	6.26
		per D	1,089	112.9	143.8	3.08		16,954	10.86
		per T	1,271	169.3	215.7	4.56		23,545	10.45
	tkL 603AN	per m wall	1,161	104.0	132.4	2.65	671	18,601	11.85
		per S	298	62.4	79.5	1.72		3,539	6.67
		per D	1,393	124.7	158.9	3.31		22,321	11.85
		per T	1,604	187.1	238.4	4.90		30,941	11.39
	tkL 603 108	per m wall	1,215	108.0	137.7	2.65	702	19,456	11.89
		per S	305	64.8	82.6	1.73		3,663	6.66
		per D	1,458	129.7	165.2	3.32		23,347	11.89
		per T	1,677	194.5	247.8	4.90		32,351	11.43

*Only on request

- 1) The elastic section modulus of the U-profiles may only be applied in the static calculation if at least every second interlock is crimped and welded to absorb the shear forces
- 2) E section modulus: for S and T related to the axis of gravity of the respective element, for D and per m wall related to the wall axis y-y

Technical data		Elastic section modulus W_y cm^3	Weight kg/m	Cross sectional area cm^2	Coating area m^2/m	Static moment S_y cm^3	Moment of inertia I_y cm^4	Radius of gyration cm
	per m wall	1,261	114.1	145.3	2.65	732	20,196	11.79
	per S	327	68.4	87.2	1.73		3,905	6.69
	per D	1,513	136.9	174.4	3.32		24,235	11.79
	per T	1,746	205.3	261.5	4.91		33,617	11.34
	per m wall	1,409	107.1	136.5	2.88	819	27,478	14.19
	per S	393	64.3	81.9	1.85		5,438	8.15
	per D	1,691	128.6	163.8	3.58		32,973	14.19
	per T	1,959	192.8	245.7	5.31		45,776	13.65
	per m wall	1,659	124.0	158.0	2.85	966	32,407	14.32
	per S	430	74.4	94.8	1.85		6,070	8.00
	per D	1,991	148.8	189.5	3.56		38,888	14.32
	per T	2,294	223.2	284.3	5.27		53,874	13.77
	per m wall	1,885	130.1	165.7	2.91	1,097	39,681	15.47
	per S	478	78.1	99.4	1.89		7,244	8.54
	per D	2,262	156.1	198.9	3.64		47,618	15.47
	per T	2,600	234.2	298.3	5.39		65,905	14.86
	per m wall	1,975	134.8	171.7	2.90	1,150	41,681	15.58
	per S	483	80.9	103.0	1.88		7,401	8.48
	per D	2,370	161.8	206.1	3.62		50,017	15.58
	per T	2,717	242.7	309.1	5.36		69,157	14.96
	per m wall	2,020	137.0	174.5	2.90	1,175	42,684	15.64
	per S	486	82.2	104.7	1.88		7,491	8.46
	per D	2,424	164.4	209.4	3.62		51,220	15.64
	per T	2,774	246.6	314.1	5.36		70,791	15.01
	per m wall	2,050	138.5	176.4	2.90	1,192	43,362	15.68
	per S	489	83.1	105.8	1.88		7,554	8.45
	per D	2,460	166.2	211.7	3.62		52,034	15.68
	per T	2,814	249.2	317.5	5.36		71,897	15.05

- 1) The elastic section modulus of the U-profiles may only be applied in the static calculation if at least every second interlock is crimped and welded to absorb the shear forces
- 2) Elastic section modulus: for S and T related to the axis of gravity of the respective element, for D and per m wall related to the wall axis y-y

Technical data		Elastic section modulus W_y cm^3	Weight kg/m	Cross sectional area cm^2	Coating area m^2/m	Static moment S_y cm^3	Moment of inertia I_y cm^4	Radius of gyration cm	
	tkL 605 N 139,2	per m wall	2,065	139.2	177.3	2.90	1,200	43,699	15.70
		per S	490	83.5	106.4	1.88		7,583	8.44
		per D	2,478	167.0	212.8	3.62		52,439	15.70
		per T	2,833	250.5	319.2	5.36		72,446	15.07
	tkL 605K	per m wall	2,068	142.9	182.0	2.91	1,207	43,434	15.45
		per S	512	85.7	109.2	1.89		7,821	8.46
		per D	2,482	171.4	218.4	3.64		52,121	15.45
		per T	2,849	257.2	327.7	5.38		72,102	14.83
	tkL 605 N +0,5	per m wall	2,094	140.5	179.0	2.90	1,217	44,350	15.74
		per S	491	84.3	107.4	1.88		7,636	8.43
		per D	2,513	168.6	214.8	3.62		53,220	15.74
		per T	2,870	252.9	322.1	5.36		73,504	15.11
	tkL 606 AS +0,5	per m wall	2,228	144.9	184.6	2.93	1,289	47,898	16.11
		per S	506	87.0	110.8	1.90		8,048	8.52
		per D	2,673	173.9	221.5	3.65		57,477	16.11
		per T	3,044	260.9	332.3	5.41		79,319	15.45
	tkL 606 A +0,5	per m wall	2,269	144.9	184.6	2.93	1,305	48,893	16.28
		per S	503	86.9	110.7	1.90		8,096	8.55
		per D	2,723	173.9	221.5	3.65		58,672	16.28
		per T	3,093	260.8	332.2	5.41		80,930	15.61
	tkL 606 AN 10	per m wall	2,402	153.4	195.4	2.92	1,389	51,913	16.30
		per S	517	92.0	117.2	1.89		8,373	8.45
		per D	2,883	184.0	234.4	3.65		62,295	16.30
		per T	3,270	276.0	351.6	5.40		85,852	15.63
	tkL 606 N 157	per m wall	2,517	157.0	200.1	2.92	1,449	54,645	16.53
		per S	520	94.3	120.1	1.89		8,560	8.44
		per D	3,020	188.5	240.1	3.65		65,574	16.53
		per T	3,414	282.8	360.2	5.40		90,286	15.83
	tkL 606 N 157	per m wall	2,517	157.0	200.1	2.92	1,449	54,645	16.53
		per S	520	94.3	120.1	1.89		8,560	8.44
		per D	3,020	188.5	240.1	3.65		65,574	16.53
		per T	3,414	282.8	360.2	5.40		90,286	15.83

- 1) The elastic section modulus of the U-profiles may only be applied in the static calculation if at least every second interlock is crimped and welded to absorb the shear forces
- 2) Elastic section modulus: for S and T related to the axis of gravity of the respective element, for D and per m wall related to the wall axis y-y

Technical data		Elastic section modulus W_y cm^3	Weight kg/m	Cross sectional area cm^2	Coating area m^2/m	Static moment S_y cm^3	Moment of inertia I_y cm^4	Radius of gyration cm	
	tkL 504A	per m wall	1,423	127.0	161.7	2.85	838	24,198	12.23
		per S	329	63.5	80.9	1.56		3,993	7.30
		per D	1,423	127.0	161.7	2.98		24,198	12.23
		per T	1,652	190.5	242.6	4.40		33,596	11.77
	tkL 504	per m wall	1,504	133.2	169.7	2.85	886	25,575	12.28
		per S	341	66.6	84.8	1.56		4,181	7.20
		per D	1,504	133.2	169.7	2.98		25,575	12.28
		per T	1,744	199.8	254.5	4.40		35,493	11.81
	tkL 504 K	per m wall	1,602	140.6	179.1	2.84	942	27,233	12.33
		per S	355	70.3	89.6	1.56		4,408	7.20
		per D	1,602	140.6	179.1	2.98		27,233	12.33
		per T	1,854	210.9	268.7	4.40		37,780	11.86
	tkL 507 A	per m wall	2,800	184.6	235.2	3.18	1,638	61,185	16.13
		per S	554	92.3	117.6	1.73		8,797	8.65
		per D	2,800	184.6	235.2	3.32		61,185	16.13
		per T	3,203	276.9	352.8	4.91		84,512	15.48
	tkL IIIIn	per m wall	1,600	155.5	198.1	3.12	928	23,206	10.82
		per S	255	62.2	79.3	1.38		2,849	5.99
		per D	1,280	124.4	158.5	2.62		18,565	10.82
		per T	1,469	186.6	237.8	3.88		25,703	10.40

- 1) The elastic section modulus of the U-profiles may only be applied in the static calculation if at least every second interlock is crimped and welded to absorb the shear forces
- 2) Elastic section modulus: for S and T related to the axis of gravity of the respective element, for D and per m wall related to the wall axis y-y

Conformity assessments

Certificate of conformity (Ü-Zeichen, ÜHP);

Proof of conformity for products of the building industry according to regulation Bauregelliste 4

Interlock forms, shapes of supply, handling holes and interlocking

Interlock

U-Section (LARSEN interlock)

Interlock form to DIN EN 10248-2
and EAU 2020




Handling holes and crimping/welding

Handling holes can be cut on request. They are cut in every pile flange according to the drawing below. The distance of the hole from the top edge is 75 or 300 mm (diameter 40mm) and must be specified with the order.

Factory crimping, factory shear-resistant welding, or site welding of the interlocks is required to achieve the section moduli of the U-sections specified in this publication. Crimped double piles are delivered with triple crimping points spaced approx. 0.6 m apart. Closer spacing can be specified for crimping points and handling holes on request. The loadbearing capacity of each triple crimping point is min. 75 kN for a mutual displacement of 5 mm. On request sheet piling can also be provided with shear-resistant welding.

Shape of supply

S

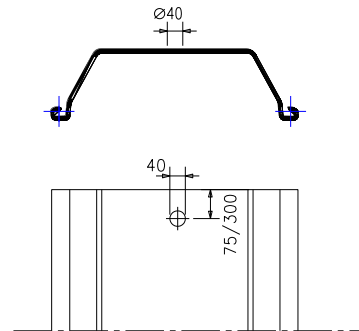

D
(S-shape)




DZ
(Z-shape is non-standard)



Z
Triple pile
on request



Overview: Z-Sections

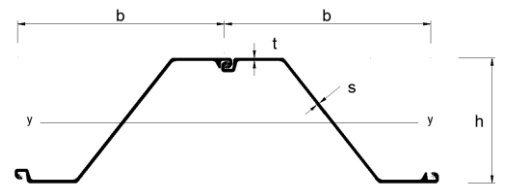

Technical data												
thyssenkrupp Sections	Elastic section modulus W_y cm^3	Plastic section modulus $W_{y,pl}$ cm^3	Weight kg/m^2	Weight Single pile kg/m	Moment of inertia I_y cm^4/m	Flange thick- ness t mm	Web thickness s mm	Height h mm	Section width b mm	Classification to DIN EN 1993-5		
										S 270 GP	S 355 GP	S 430 GP
Hoesch 1207	1,205	1,415	96.6	67.6	18,833	8.6	8.5	312.5	700	3	3	3
Hoesch 1307	1,307	1,541	105.6	73.9	20,494	9.6	9.5	313.5	700	2	3	3
Hoesch 1407	1,409	1,667	114.7	80.3	22,156	10.6	10.5	314.5	700	2	2	3
Hoesch 1707	1,731	2,031	104.6	73.2	36,304	8.5	8.5	419.5	700	3	3	3
Hoesch 1807	1,804	2,120	109.5	76.7	37,894	9.0	9.0	420.0	700	2	3	3
Hoesch 1907	1,878	2,213	114.5	80.1	39,485	9.5	9.5	420.5	700	2	3	3
Hoesch 2007	1,951	2,302	119.4	83.6	41,076	10.0	10.0	421.0	700	2	3	3
Hoesch 2407	2,432	2,818	135.9	95.1	53,379	11.0	11.0	439.0	700	2	3	3
Hoesch 2607	2,606	3,030	146.5	102.5	57,329	12.0	12.0	440.0	700	2	2	3
Hoesch 2807	2,779	3,240	157.0	109.9	61,279	13.0	13.0	441.0	700	2	2	2
Hoesch 3607	3,600	4,111	168.8	118.1	89,826	17.0	11.0	499.0	700	2	2	2
Hoesch 3807	3,800	4,357	179.9	125.9	95,004	18.0	12.0	500.0	700	2	2	2
Hoesch 4007	3,999	4,604	191.0	133.7	100,184	19.0	13.0	501.0	700	2	2	2

Details: Z-Sections

Sections

S = Single pile

D = Double pile

Technical data		Elastic section modulus W_y cm ³	Weight kg/m	Cross sectional area cm ²	Coating area m ² /m	Static moment S_y cm ³	Moment of inertia I_y cm ⁴	Radius of gyration cm
	per m wall	1,205	96.6	123.1	1.22	708	18,833	12.37
	per S	843	67.6	86.1	0.86		13,183	12.37
	per D	1,687	135.2	172.3	1.71		26,366	12.37
	per m wall	1,307	105.6	134.6	1.22	770	20,494	12.34
	per S	915	73.9	94.2	0.86		14,346	12.34
	per D	1,830	147.9	188.4	1.71		28,692	12.34
	per m wall	1,409	114.7	146.1	1.22	834	22,156	12.31
	per S	985	80.3	102.3	0.86		15,510	12.31
	per D	1,973	160.6	204.6	1.71		31,019	12.31
	per m wall	1,731	104.6	133.2	1.33	1,015	36,304	16.51
	per S	1,209	73.2	93.3	0.93		25,413	16.51
	per D	2,423	146.4	186.5	1.87		50,826	16.51
	per m wall	1,804	109.5	139.5	1.33	1,060	37,894	16.48
	per S	1,261	76.7	97.7	0.93		26,526	16.48
	per D	2,526	153.3	195.3	1.87		53,052	16.48
	per m wall	1,878	114.5	145.9	1.33	1,106	39,485	16.45
	per S	1,313	80.1	102.1	0.93		27,640	16.45
	per D	2,629	160.3	204.2	1.87		55,279	16.45

Technical data		Elastic section modulus W_y cm^3	Weight kg/m	Cross sectional area cm^2	Coating area m^2/m	Static moment S_y cm^3	Moment of inertia I_y cm^4	Radius of gyration cm
	per m wall	1,951	119.4	152.5	1.33	1.151	41,076	16.43
	per S	1,366	83.6	106.5	0.93		28,754	16.43
	per D	2,732	167.2	213.0	1.87		57,507	16.43
	per m wall	2,432	135.9	173.1	1.39	1.409	53,379	17.56
	per S	1,701	95.1	121.2	0.97		37,365	17.56
	per D	3,405	190.2	242.4	1.95		74,730	17.56
	per m wall	2,606	146.5	186.6	1.39	1.515	57,329	17.53
	per S	1,824	102.5	130.6	0.97		40,130	17.53
	per D	3,648	205.0	261.2	1.95		80,260	17.53
	per m wall	2,779	157.0	200.0	1.39	1.620	61,279	17.50
	per S	1,945	109.9	140.0	0.97		42,896	17.50
	per D	3,891	219.8	280.0	1.95		85,791	17.50
	per m wall	3,600	168.8	215.0	1.45	2.056	89,826	20.44
	per S	2,515	118.1	150.5	1.02		62,878	20.44
	per D	5,040	236.3	301.1	2.03		125,757	20.44
	per m wall	3,800	179.9	229.2	1.45	2.179	95,004	20.36
	per S	2,654	125.9	160.4	1.02		66,503	20.36
	per D	5,320	251.9	320.9	2.03		133,006	20.36
	per m wall	3,999	191.0	243.3	1.45	2.302	100,184	20.29
	per S	2,792	133.7	170.3	1.02		70,128	20.29
	per D	5,599	267.4	340.7	2.03		140,258	20.29

Conformity assessments

Certificate of conformity (Ü-Zeichen, ÜHP);

Proof of conformity for products of the building industry according to regulation Bauregelliste 4

Interlock forms, shapes of supply, handling holes and interlocking

Interlock

Z-Section

(LARSEN interlock)

Interlock form to DIN EN 10248-2 and EAU 2020



Handling holes and crimping/welding


Handling holes can be cut on request. They are cut in every pile flange according to the drawing below. The distance of the hole from the top edge is 75 or 300 mm and must be specified with the order. Crimping/welding of double piles on request.

Shape of supply


Eb






Ea



Db

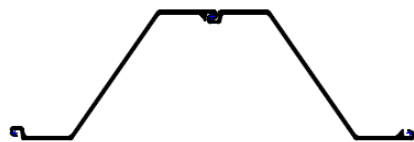


Da

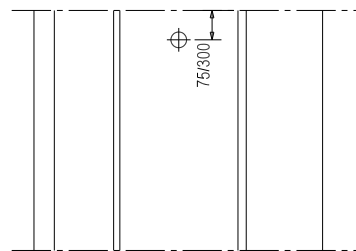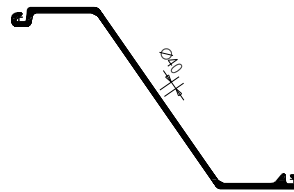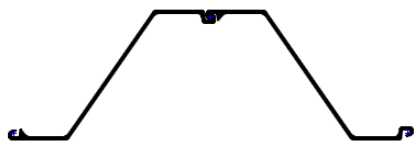


Steel box piles

Technical data

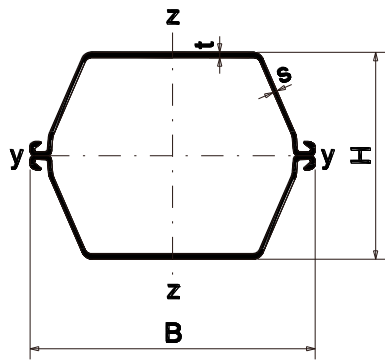

thyssenkrupp LP

Pile sections	Section modulus W_y cm ³	Section modulus W_z cm ³	Weight kg/m	b mm	h mm	Dimensions t mm s mm		Perimeter cm	Area Steel cross section cm ²	Moment of inertia I_y cm ⁴	Moment of inertia I_z cm ⁴	Radius of gyration min.i cm
LP 601	1,047	1,532	92.6	632	348	7.5	6.4	188	118.0	18,229	48,407	12.43
LP 602	1,197	1,771	106.8	633	350	8.4	7.6	188	136.0	20,976	56,067	12.42
LP 603	1,692	2,209	128.4	638	363	9.6	8.2	202	163.6	30,718	70,370	13.70
LP 603 Z	1,863	2,554	144.2	638	369	10.0	10.0	202	183.7	34,350	81,479	13.67
LP 604 A	2,161	2,525	142.0	638	435	9.6	8.8	214	181.0	46,946	80,555	16.10
LP 604	2,238	2,582	146.2	638	435	10.0	9.0	214	186.3	48,661	82,354	16.16
LP 605 N	2,764	2,753	164.2	638	467	12.0	9.5	219	209.2	64,607	87,814	17.57
LP 605 KN	2,898	2,848	171.2	638	469	12.6	10.0	219	218.1	67,950	90,864	17.65
LP 606 A	3,006	2,748	170.8	638	475	13.4	9.0	219	217.6	71,383	87,654	18.11
LP 606 N	3,414	2,925	188.2	638	479	15.4	9.8	220	239.7	81,740	93,307	18.47
LP 628	3,854	3,127	203.6	638	501	16.3	10.1	224	259.3	96,479	99,740	19.29
LP 607 A	4,033	3,193	212.4	638	499	17.7	10.0	222	270.7	100,704	101,843	19.29
LP 607	4,190	3,427	224.8	638	502	19.0	10.6	223	286.3	105,163	109,326	19.17
LP 607 K	4,290	3,605	233.6	638	504	20.0	11.0	223	297.5	108,118	114,994	19.06



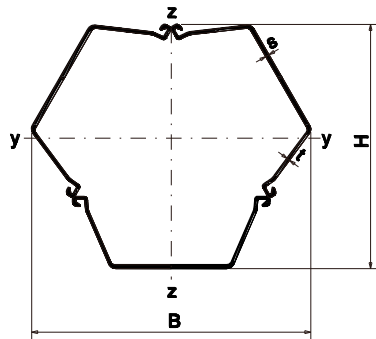


thyssenkrupp LD

LD 601	3,000	2,999	138.9	745	724	7.5	6.4	278	177.0	111,704	111,704	25.12
LD 602	3,457	3,454	204.0	747	727	8.4	7.6	279	204.0	129,056	129,056	25.15
LD 603	4,450	4,097	192.6	818	737	9.6	8.2	299	245.3	167,522	167,522	26.13
LD 603 Z	5,022	4,612	216.3	823	741	10.0	10.0	300	275.6	189,690	189,690	26.24
LD 604 A	5,223	4,709	213.0	879	773	9.6	8.8	317	271.5	207,010	207,010	27.61
LD 604	5,379	4,850	219.3	879	773	10.0	9.0	317	279.4	213,276	213,276	27.63
LD 605 N	6,085	5,573	246.3	901	791	12.0	9.5	324	313.8	251,195	251,195	28.29
LD 605 KN	6,346	5,817	256.8	902	791	12.6	10.0	325	327.1	262,422	262,422	28.32
LD 606 A	6,359	5,850	256.2	906	794	13.4	9.0	326	326.4	264,870	264,870	28.49
LD 606 N	7,041	6,483	282.3	909	796	15.4	9.8	327	359.6	294,669	294,669	28.63
LD 628	7,664	7,083	305.4	929	809	16.3	10.1	332	389.0	329,063	329,063	29.08
LD 607 A	8,004	7,453	318.6	921	806	17.7	10.0	330	406.0	343,170	343,170	29.07
LD 607	8,478	7,898	337.2	923	807	19.0	10.6	331	429.5	364,602	364,602	29.14
LD 607 K	8,822	8,223	350.4	925	808	20.0	11.0	331	446.3	380,300	380,300	29.19


- 1) Further (special) sections on request
- 2) Steel plates can be additionally welded on to increase the static values

Technical Data

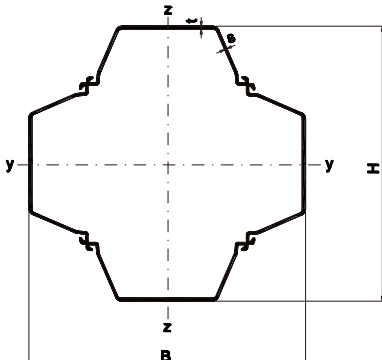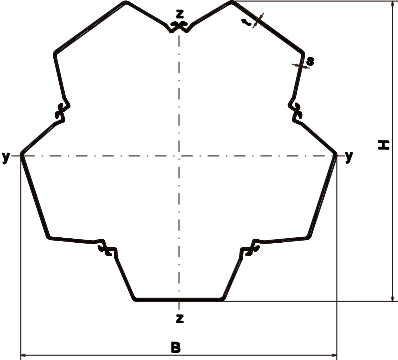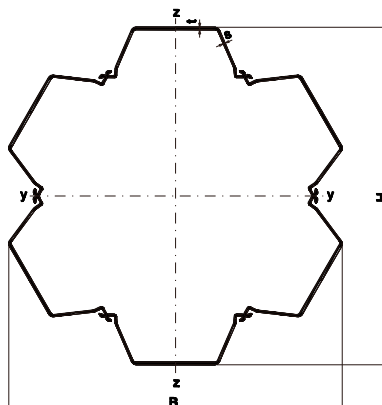	Pile sections	Section modulus W_y cm ³	Section modulus W_z cm ³	Weight kg/m	b mm	H mm	Dimensions t mm	s mm	Perimeter cm	Area Steel cross section cm ²	Moment of inertia I_y cm ⁴	Moment of inertia I_z cm ⁴	Radius of gyration min. i cm
thyssenkrupp LV													
	LV 601	5,335	185.2	968	968	7.5	6.4	369	236.0	258,198	33.08		
	LV 602	6,145	213.6	971	971	8.4	7.6	369	272.0	298,312	33.12		
	LV 603	7,744	256.8	986	986	9.6	8.2	397	327.1	381,896	34.17		
	LV 603 Z	8,684	288.4	993	993	10.0	10.0	398	367.4	431,074	34.25		
	LV 604 A	8,718	284.0	1,059	1,059	9.6	8.8	421	362.0	461,491	35.70		
	LV 604	8,982	292.4	1,059	1,059	10.0	9.0	421	372.6	475,644	35.73		
	LV 605 N	10,211	328.4	1,092	1,092	12.0	9.5	430	418.5	557,375	36.49		
	LV 605 KN	10,656	342.4	1,093	1,093	12.6	10.0	431	436.2	582,398	36.54		
	LV 606 A	10,695	341.6	1,099	1,099	13.4	9.0	432	435.2	587,726	36.75		
	LV 606 N	11,863	376.4	1,103	1,103	15.4	9.8	433	479.5	654,278	36.94		
	LV 628	12,920	407.2	1,125	1,125	16.3	10.1	441	518.7	726,613	37.43		
	LV 607 A	13,517	424.8	1,124	1,124	17.7	10.0	438	541.3	759,384	37.46		
	LV 607	14,329	449.6	1,126	1,126	19.0	10.6	439	572.6	806,845	37.54		
	LV 607 K	14,919	467.2	1,128	1,128	20.0	11.0	440	595.1	841,559	37.61		
thyssenkrupp LF													
	LF 604 A	13,176	12,645	355.0	1,352	1,290	9.6	8.8	524	452.5	856,845	854,275	43,45
	LF 604	13,524	12,966	365.5	1,352	1,290	10.0	9.0	524	465.5	879,595	876,751	43,40
	LF 605 N	15,409	14,859	410.5	1,379	1,314	12.0	9.5	532	523.0	1,024,299	1,024,823	44,26
	LF 605 KN	16,069	15,486	428.0	1,379	1,314	12.6	10.0	532	545.5	1,068,055	1,068,090	44,25
	LF 606 A	16,087	15,508	427.0	1,382	1,318	13.4	9.0	537	544.0	1,075,901	1,071,598	44,38
	LF 606 N	17,885	17,304	470.5	1,386	1,323	15.4	9.8	537	599.5	1,200,892	1,197,124	44,69
	LF 628	19,455	18,763	509.0	1,406	1,345	16.3	10.1	545	648.5	1,330,228	1,319,432	45,11
	LF 607 A	20,462	19,754	531.0	1,401	1,340	17.7	10.0	544	676.5	1,395,953	1,384,162	45,23
	LF 607	21,637	20,975	562.0	1,404	1,342	19.0	10.6	544	716.0	1,478,955	1,472,440	45,35
	LF 607 K	22,539	21,869	584.0	1,406	1,344	20.0	11.0	544	744.0	1,543,947	1,537,415	45,46
thyssenkrupp LS													
	LS 604 A	18,121	18,962	426.0	1,504	1,535	9.6	8.8	632	543.0	1,390,812	1,425,933	50.61
	LS 604	18,589	19,476	438.6	1,504	1,535	10.0	9.0	632	558.6	1,427,288	1,464,623	50.55
	LS 605 N	21,220	22,397	492.6	1,530	1,561	12.0	9.5	638	627.6	1,665,526	1,713,384	51.36
	LS 605 KN	22,139	23,345	513.6	1,530	1,561	12.6	10.0	638	654.6	1,727,179	1,785,918	51.37
	LS 606 A	22,198	23,191	512.4	1,536	1,569	13.4	9.0	643	652.8	1,745,858	1,767,140	51.71
	LS 606 N	24,686	26,021	564.6	1,540	1,571	15.4	9.8	643	719.4	1,938,243	2,002,728	51.91
	LS 628	26,879	28,165	610.8	1,556	1,596	16.3	10.1	654	778.2	2,144,918	2,191,217	52.50
	LS 607 A	28,182	29,642	637.2	1,548	1,592	17.7	10.0	650	811.8	2,244,228	2,294,323	52.58
	LS 607	29,841	31,434	674.4	1,552	1,595	19.0	10.6	650	859.2	2,379,842	2,439,270	52.63
	LS 607 K	31,090	32,782	700.8	1,554	1,597	20.0	11.0	650	892.8	2,482,569	2,547,128	52.73


1) Further (special) sections on request
 2) Steel plates can be additionally welded on to increase the static values

Combined sheet pile walls

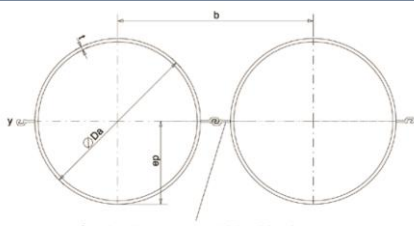Technical data									
Pipe pile wall with LPB 180-12 connector	Pipe diameter	Wall thickness	Width	Moment of inertia	Section modulus	Edge distance	Deadweight related to pipe length - Length of connector LPB 180 as % of pipe length	Coating area	
	Da mm	t mm	b (m)	I_y cm ⁴ /m	W_y cm ³ /m	ep cm	100% kg/m ²	Water site m ² /m	
 <p>Steelwall connectors LPB 180-12</p>	813	10.00	0,993	204,797	5,038	40.65	228.63	1.50	
	813	12.00	0,993	243,942	6,001	40.65	267.92	1.50	
	813	14.00	0,993	282,496	6,949	40.65	307.01	1.50	
	819	10.00	0,999	208,164	5,083	40.95	228.74	1.50	
	819	12.00	0,999	247,966	6,055	40.95	268.09	1.50	
	819	14.00	0,999	287,172	7,013	40.95	307.24	1.50	
	914	10.00	1,094	265,217	5,803	45.70	230.29	1.50	
	914	12.00	1,094	316,170	6,918	45.70	270.51	1.50	
	914	14.00	1,094	366,440	8,018	45.70	310.54	1.50	
	1,016	10.00	1,196	334,322	6,581	50.80	231.68	1.51	
	1,016	12.00	1,196	398,817	7,851	50.80	272.68	1.51	
	1,016	14.00	1,196	462,535	9,105	50.80	313.50	1.51	
	1,220	12.00	1,400	593,413	9,728	61.00	276.07	1.52	
	1,220	14.00	1,400	688,907	11,294	61.00	318.13	1.52	
	1,220	16.00	1,400	783,444	12,843	61.00	360.06	1.52	
	1,420	14.00	1,600	955,140	13,453	71.00	321.52	1.53	
	1,420	16.00	1,600	1,086,970	15,309	71.00	364.37	1.53	
	1,420	18.00	1,600	1,217,666	17,150	71.00	407.10	1.53	
	1,620	16.00	1,800	1,440,667	17,786	81.00	367.73	1.53	
	1,620	18.00	1,800	1,614,739	19,935	81.00	411.19	1.53	
1,620	20.00	1,800	1,787,496	22,068	81.00	454.54	1.53		
1,820	18.00	2,000	2,068,284	22,728	91.00	414.46	1.53		
1,820	20.00	2,000	2,290,504	25,170	91.00	458.41	1.53		
1,820	22.00	2,000	2,511,231	27,596	91.00	502.26	1.53		
1,820	25.00	2,000	2,839,537	31,204	91.00	567.84	1.53		

Technical data

Pipe / sheet pile wall with tkL 603 double pile intermediate piles

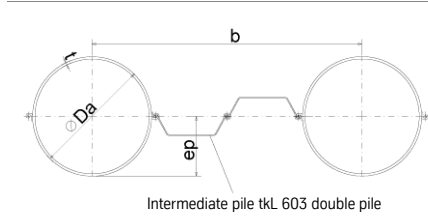


Pipe diameter Da mm	Wall thickness t mm	Width b m	Including intermediate piles		Excluding intermediate piles		Edge distance ep cm	Deadweight related to pipe length - Length of connector as % of pipe length			Coating area ly m ² /m
			Moment of inertia I _y cm ⁴ /m	Section modulus W _y cm ³ /m	Moment of inertia I _y cm ⁴ /m	Section modulus W _y cm ³ /m		Da kg/m ²	t kg/m ²	b kg/m ²	
813	10.00	2,073	109,216	2,687	98,101	2,413	40.65	138.83	153.26	167.70	1.41
813	12.00	2,073	127,967	3,148	116,852	2,875	40.65	157.65	172.08	186.52	1.41
813	14.00	2,073	146,434	3,602	135,320	3,329	40.65	176.37	190.81	205.24	1.41
819	10.00	2,079	111,109	2,713	100,027	2,443	40.95	139.14	153.53	167.92	1.41
819	12.00	2,079	130,235	3,180	119,153	2,910	40.95	158.05	172.44	186.83	1.41
819	14.00	2,079	149,074	3,640	137,992	3,370	40.95	176.86	191.25	205.64	1.41
914	10.00	2,174	144,060	3,152	133,462	2,920	45.70	143.84	157.60	171.36	1.42
914	12.00	2,174	169,701	3,713	159,103	3,481	45.70	164.07	177.84	191.60	1.42
914	14.00	2,174	194,998	4,267	184,400	4,035	45.70	184.22	197.98	211.75	1.42
1,016	10.00	2,276	185,804	3,658	175,681	3,458	50.80	148.44	161.59	174.73	1.43
1,016	12.00	2,276	219,694	4,325	209,571	4,125	50.80	169.98	183.13	196.27	1.43
1,016	14.00	2,276	253,177	4,984	243,054	4,785	50.80	191.44	204.58	217.73	1.43
1,220	12.00	2,480	344,281	5,644	334,991	5,492	61.00	180.34	192.41	204.47	1.44
1,220	14.00	2,480	398,189	6,528	388,899	6,375	61.00	204.09	216.16	228.22	1.44
1,220	16.00	2,480	451,557	7,403	442,267	7,250	61.00	227.76	239.82	251.89	1.44
1,420	14.00	2,680	578,830	8,153	570,233	8,031	71.00	214.63	225.79	236.95	1.45
1,420	16.00	2,680	657,534	9,261	648,937	9,140	71.00	240.21	251.37	262.54	1.45
1,420	18.00	2,680	735,562	10,360	726,965	10,239	71.00	265.72	276.88	288.04	1.45
1,620	16.00	2,880	908,417	11,215	900,417	11,116	81.00	250.93	261.32	271.71	1.46
1,620	18.00	2,880	1,017,212	12,558	1,009,212	12,459	81.00	278.09	288.48	298.87	1.46
1,620	20.00	2,880	1,125,185	13,891	1,117,185	13,792	81.00	305.18	315.57	325.96	1.46
1,820	18.00	3,080	1,350,522	14,841	1,343,041	14,759	91.00	288.86	298.57	308.29	1.46
1,820	20.00	3,080	1,494,821	16,427	1,487,340	16,344	91.00	317.39	327.11	336.82	1.46
1,820	22.00	3,080	1,638,150	18,002	1,630,669	17,919	91.00	345.87	355.58	365.30	1.46
1,820	25.00	3,080	1,851,336	20,344	1,843,855	20,262	91.00	388.46	398.17	407.88	1.46

Other intermediate piles on request

Technical data

Pipe / sheet pile wall with tkL 603 triple pile intermediate piles

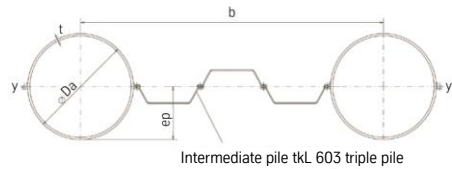


Pipe diameter Da mm	Wall thickness t mm	Width b m	Including intermediate piles		Excluding intermediate piles		Edge distance ep cm	Deadweight related to pipe length - Length of connector as % of pipe length			Coating area I _y m ² /m
			Moment of inertia I _y cm ⁴ /m	Section modulus W _y cm ³ /m	Moment of inertia I _y cm ⁴ /m	Section modulus W _y cm ³ /m		Da kg/m ²	t kg/m ²	b kg/m ²	
813	10.00	2,673	88,000	2,165	76,081	1,872	40.65	122.08	138.07	154.07	1.38
813	12.00	2,673	102,542	2,523	90,623	2,229	40.65	136.67	152.67	168.67	1.38
813	14.00	2,673	116,864	2,875	104,945	2,582	40.65	151.19	167.19	183.19	1.38
819	10.00	2,679	89,517	2,186	77,625	1,896	40.95	122.36	138.32	154.28	1.39
819	12.00	2,679	104,359	2,548	92,467	2,258	40.95	137.03	152.99	168.95	1.39
819	14.00	2,679	118,979	2,905	107,086	2,615	40.95	151.63	167.59	183.55	1.39
914	10.00	2,774	116,080	2,540	104,595	2,289	45.70	126.61	142.03	157.44	1.39
914	12.00	2,774	136,175	2,980	124,690	2,728	45.70	142.47	157.89	173.30	1.39
914	14.00	2,774	156,001	3,414	144,515	3,162	45.70	158.26	173.68	189.09	1.39
1,016	10.00	2,876	150,108	2,955	139,030	2,737	50.80	130.87	145.74	160.60	1.40
1,016	12.00	2,876	176,928	3,483	165,850	3,265	50.80	147.91	162.78	177.65	1.40
1,016	14.00	2,876	203,426	4,004	192,348	3,786	50.80	164.89	179.76	194.63	1.40
1,220	12.00	3,080	280,077	4,591	269,733	4,422	61.00	157.72	171.60	185.48	1.41
1,220	14.00	3,080	323,484	5,303	313,139	5,133	61.00	176.84	190.72	204.61	1.41
1,220	16.00	3,080	366,455	6,007	356,111	5,838	61.00	195.90	209.78	223.66	1.41
1,420	14.00	3,280	475,635	6,699	465,922	6,562	71.00	187.11	200.15	213.18	1.42
1,420	16.00	3,280	539,943	7,605	530,229	7,468	71.00	208.01	221.05	234.08	1.42
1,420	18.00	3,280	603,697	8,503	593,983	8,366	71.00	228.85	241.89	254.93	1.42
1,620	16.00	3,480	754,328	9,313	745,173	9,200	81.00	218.73	231.02	243.31	1.43
1,620	18.00	3,480	844,365	10,424	835,210	10,311	81.00	241.21	253.50	265.79	1.43
1,620	20.00	3,480	933,722	11,527	924,567	11,414	81.00	263.63	275.92	288.21	1.43
1,820	18.00	3,680	1,132,725	12,448	1,124,067	12,352	91.00	252.23	263.85	275.47	1.44
1,820	20.00	3,680	1,253,497	13,775	1,244,839	13,680	91.00	276.11	287.73	299.35	1.44
1,820	22.00	3,680	1,373,457	15,093	1,364,799	14,998	91.00	299.94	311.56	323.18	1.44
1,820	25.00	3,680	1,551,884	17,054	1,543,226	16,959	91.00	335.59	347.21	358.83	1.44

Other intermediate piles on request

Technical data


Pipe / sheet pile wall with Hoesch 1807 double pile intermediate piles

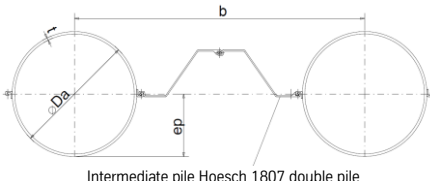	Pipe diameter Da mm	Wall thickness t mm	Width b m	Including intermediate piles		Excluding intermediate piles		Edge distance ep cm	Deadweight related to pipe length - Length of connector as % of pipe length			Coating area I _y m ² /m
				Moment of inertia I _y cm ⁴ /m	Section modulus W _y cm ³ /m	Moment of inertia I _y cm ⁴ /m	Section modulus W _y cm ³ /m		Da kg/m ²	t kg/m ²	b kg/m ²	
	813	10.00	2,273	112,875	2,777	89,469	2,201	40.65	132.47	147.59	162.71	1.38
	813	12.00	2,273	129,976	3,197	106,570	2,622	40.65	149.64	164.75	179.87	1.38
	813	14.00	2,273	146,819	3,612	123,413	3,036	40.65	166.72	181.83	196.95	1.38
	819	10.00	2,279	114,593	2,798	91,249	2,228	40.95	132.77	147.85	162.93	1.38
	819	12.00	2,279	132,040	3,224	108,696	2,654	40.95	150.02	165.10	180.18	1.38
	819	14.00	2,279	149,226	3,644	125,882	3,074	40.95	167.19	182.26	197.34	1.38
	914	10.00	2,374	144,629	3,165	122,219	2,674	45.70	137.33	151.80	166.28	1.39
	914	12.00	2,374	168,109	3,679	145,699	3,188	45.70	155.86	170.34	184.81	1.39
	914	14.00	2,374	191,275	4,185	168,865	3,695	45.70	174.31	188.78	203.26	1.39
	1,016	10.00	2,476	182,977	3,602	161,490	3,179	50.80	141.83	155.71	169.59	1.40
	1,016	12.00	2,476	214,130	4,215	192,643	3,792	50.80	161.63	175.51	189.39	1.40
	1,016	14.00	2,476	244,908	4,821	223,422	4,398	50.80	181.35	195.23	209.11	1.40
	1,220	12.00	2,680	329,843	5,407	309,992	5,082	61.00	171.86	184.68	197.50	1.41
	1,220	14.00	2,680	379,728	6,225	359,877	5,900	61.00	193.83	206.65	219.47	1.41
	1,220	16.00	2,680	429,113	7,035	409,262	6,709	61.00	215.73	228.55	241.37	1.41
	1,420	14.00	2,880	549,106	7,734	530,633	7,474	71.00	204.35	216.28	228.21	1.42
	1,420	16.00	2,880	622,345	8,765	603,872	8,505	71.00	228.15	240.08	252.01	1.42
	1,420	18.00	2,880	694,953	9,788	676,481	9,528	71.00	251.89	263.82	275.75	1.42
	1,620	16.00	3,080	859,221	10,608	841,948	10,394	81.00	238.96	250.11	261.27	1.43
	1,620	18.00	3,080	960,951	11,864	943,678	11,650	81.00	264.36	275.51	286.67	1.43
	1,620	20.00	3,080	1,061,914	13,110	1,044,641	12,897	81.00	289.69	300.85	312.00	1.43
	1,820	18.00	3,280	1,277,368	14,037	1,261,149	13,859	91.00	275.31	285.78	296.26	1.44
	1,820	20.00	3,280	1,412,868	15,526	1,396,649	15,348	91.00	302.10	312.58	323.05	1.44
	1,820	22.00	3,280	1,547,458	17,005	1,531,238	16,827	91.00	328.84	339.31	349.79	1.44
	1,820	25.00	3,280	1,747,645	19,205	1,731,425	19,027	91.00	368.83	379.31	389.78	1.44

Other intermediate piles on request

Technical data

Pipe / sheet pile wall with Hoesch 1907 double pile intermediate piles

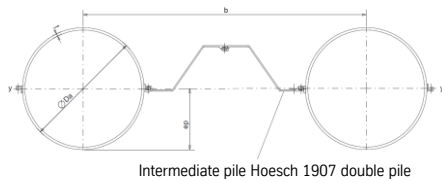



Intermediate pile Hoesch 1907 double pile


Pipe diameter Da mm	Wall thickness t mm	Width b m	Including intermediate piles		Excluding intermediate piles		Edge distance ep cm	Deadweight related to pipe length - Length of connector as % of pipe length			Coating area I _y m ² /m
			Moment of inertia I _y cm ⁴ /m	Section modulus W _y cm ³ /m	Moment of inertia I _y cm ⁴ /m	Section modulus W _y cm ³ /m		Da kg/m ²	t kg/m ²	b kg/m ²	
813	10.00	2,273	113,846	2,801	89,469	2,201	40.65	134.32	150.05	165.79	1.38
813	12.00	2,273	130,947	3,221	106,570	2,622	40.65	151.49	167.22	182.95	1.38
813	14.00	2,273	147,790	3,636	123,413	3,036	40.65	168.56	184.30	200.03	1.38
819	10.00	2,279	115,562	2,822	91,249	2,228	40.95	134.62	150.31	166.00	1.38
819	12.00	2,279	133,009	3,248	108,696	2,654	40.95	151.87	167.56	183.25	1.38
819	14.00	2,279	150,195	3,668	125,882	3,074	40.95	169.03	184.72	200.41	1.38
914	10.00	2,374	145,559	3,185	122,219	2,674	45.70	139.10	154.16	169.22	1.39
914	12.00	2,374	169,039	3,699	145,699	3,188	45.70	157.63	172.69	187.76	1.39
914	14.00	2,374	192,205	4,206	168,865	3,695	45.70	176.08	191.14	206.21	1.39
1,016	10.00	2,476	183,869	3,619	161,490	3,179	50.80	143.53	157.97	172.41	1.40
1,016	12.00	2,476	215,022	4,233	192,643	3,792	50.80	163.33	177.77	192.21	1.40
1,016	14.00	2,476	245,800	4,839	223,422	4,398	50.80	183.05	197.49	211.94	1.40
1,220	12.00	2,680	330,667	5,421	309,992	5,082	61.00	173.42	186.77	200.11	1.41
1,220	14.00	2,680	380,552	6,239	359,877	5,900	61.00	195.40	208.74	222.08	1.41
1,220	16.00	2,680	429,937	7,048	409,262	6,709	61.00	217.30	230.64	243.98	1.41
1,420	14.00	2,880	549,872	7,745	530,633	7,474	71.00	205.80	218.22	230.64	1.42
1,420	16.00	2,880	623,112	8,776	603,872	8,505	71.00	229.61	242.03	254.44	1.42
1,420	18.00	2,880	695,720	9,799	676,481	9,528	71.00	253.35	265.76	278.18	1.42
1,620	16.00	3,080	859,938	10,617	841,948	10,394	81.00	240.32	251.93	263.54	1.43
1,620	18.00	3,080	961,668	11,872	943,678	11,650	81.00	265.72	277.33	288.94	1.43
1,620	20.00	3,080	1,062,631	13,119	1,044,641	12,897	81.00	291.05	302.66	314.28	1.43
1,820	18.00	3,280	1,278,042	14,044	1,261,149	13,859	91.00	276.59	287.49	298.39	1.44
1,820	20.00	3,280	1,413,542	15,533	1,396,649	15,348	91.00	303.38	314.28	325.19	1.44
1,820	22.00	3,280	1,548,131	17,012	1,531,238	16,827	91.00	330.12	341.02	351.92	1.44
1,820	25.00	3,280	1,748,318	19,212	1,731,425	19,027	91.00	370.11	381.01	391.92	1.44

Other intermediate piles on request

Cold-rolled sheet piling sections Trench sheeting

Technical Data									
Trench sheeting sections		Section modulus W_y cm^3/m	Weight Wall kg/m^2	Weight Single pile kg/m	Moment of inertia I_y cm^4/m	Width b mm	Height h mm	Flange thickness t mm	Web thickness s mm
	KD VI/6	182	62.5	37.5	726	600	78	6.0	6.0
	KD VI/8	242	83.3	50.0	968	600	80	8.0	8.0

Technical Data									
Trench sheeting sections		Section modulus W_y cm^3/m	Weight Wall kg/m^2	Weight Single pile kg/m	Moment of inertia I_y cm^4/m	Width b mm	Height h mm	Flange thickness t mm	Web thickness s mm
	KD 4L	99	53.3	21.3	245	400	49	5.8	5.8

Technical Data									
Lightweight sections		Section modulus W_y cm^3/m	Weight Wall kg/m^2	Weight Single pile kg/m	Moment of inertia I_y cm^4/m	Width b mm	Height h mm	Flange thickness t mm	Web thickness s mm
	KL 3/4*	276	45.2	31.6	2.042	700	146	4.0	4.0
	KL 3/5*	339	55.8	39.1	2.502	700	147	5.0	5.0
	KL 3/6	410	66.0	46.2	3.080	700	148	6.0	6.0
	KL 3/7*	460	78.0	54.6	3.500	700	149	7.0	7.0
	KL 3/8	540	88.0	61.5	4.050	700	150	8.0	8.0


*Only on request

Trench sheeting, Technical data

Forms of supply for trench sheeting


S

KD VI/6
KD VI/8

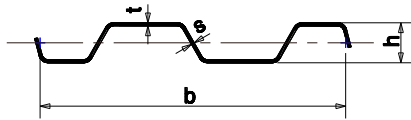


S

KD 4.4L



Handling holes, KD VI/6 and KD VI/8 trench sheets

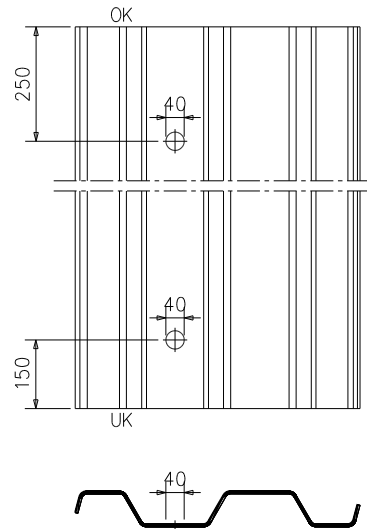

Trench sheeting is only supplied as single piles (S) with handling holes.

Handling holes KD VI/6 and KD VI/8 trench sheets

250 mm from top edge

150 mm from bottom edge, standard form

Handling holes KD 4L

250 mm from top edge


150 mm from bottom edge, standard form

Typical application: Dike protection – lightweight sections

Lightweight sections, Technical data


Forms of supply for KL lightweight sections

Sa



Single pile in A-position (non-standard form)

Sb



Single pile in B-position (standard form)

Da




Double piles (Da) to special order only

Db



Double piles (Db) to special order only

Handling holes KL lightweight sections

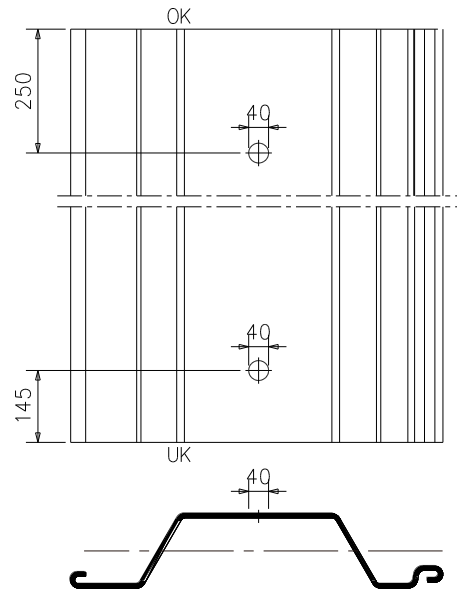

The KL lightweight sections are supplied with handling holes. Handling holes are provided at both ends according to the above drawing.

Terms of delivery and steel grades

Terms of delivery

The terms of delivery and tolerances for hot-rolled steel sheet piles are in accordance with DIN EN 10248.

Cold-rolled sheet piles are supplied in steel grade S 275 JR to DIN EN 10249.

Excerpt from the tolerances for form and dimensions for hot-rolled sheet piling made from unalloyed steels to DIN EN 10248-2

Wall thickness U-sections	t: $\leq 8.5 \text{ mm} = \pm 0.5 \text{ mm}$; $> 8.5 \text{ mm} = \pm 6 \% t$ s: $\leq 8.5 \text{ mm} = -0.5 \text{ mm}$; $> 8.5 \text{ mm} = -6 \% s^*$
Wall thickness, Z-sections and straight-web sections	t, s: $\leq 8.5 \text{ mm} = \pm 0.5 \text{ mm}$; $> 8.5 \text{ mm} = \pm 6 \% t$, t
Section width	Single pile $\pm 2 \%$, double pile $\pm 3 \%$
Section length	Lengths of sections may deviate by $\pm 200 \text{ mm}$ from ordered lengths
Section height, U-sections	$\leq 200 \text{ mm} = \pm 4 \text{ mm}$; $> 200 \text{ mm} = \pm 5 \text{ mm}$
Section height, Z-sections	$\leq 200 \text{ mm} = \pm 5 \text{ mm}$; from 200 to 300 mm = $\pm 6 \text{ mm}$; $> 300 \text{ mm} = \pm 7 \text{ mm}$
Weight	max. $\pm 5\%$ margin between calculated weight (according to section tables) and measured weight of total delivery

* Positive tolerances are usually a matter for the manufacturer's discretion. Positive tolerances can be agreed upon placing an order. In this case the following values should be used: $+0.5 \text{ mm}$ for $s < 8.5 \text{ mm}$ and $+6\%$ of s for $s > 8.5 \text{ mm}$

Excerpt from the tolerances for form and dimensions for cold-rolled sheet piling made from unalloyed steels to DIN EN 10249-2

Wall thickness for nominal width up to 1,200 mm	from 4.00 to 5.00 mm = $\pm 0.24 \text{ mm}$; from 5.00 to 6.00 mm = $\pm 0.26 \text{ mm}$; from 6.00 to 8.00 mm = $\pm 0.29 \text{ mm}$
Wall thickness for nominal width 1,200 to 1,500 mm	from 4.00 to 5.00 mm = $\pm 0.26 \text{ mm}$; from 5.00 to 6.00 mm = $\pm 0.28 \text{ mm}$;
Section width	Single pile $\pm 2 \%$, double pile $\pm 3 \%$
Section length	Lengths of sections may deviate by $\pm 50 \text{ mm}$ from ordered lengths
Section height	$\leq 200 \text{ mm}$ section height $\pm 4 \text{ mm}$
Weight	max. $\pm 7\%$ margin between calculated weight (according to section tables) and measured weight of total delivery

All data and contents are without guarantee.
Mistake and subject to change.

Steel grade

The steel grades used for our hot-rolled steel sheet piles comply with DIN EN 10248-1.

Hot-rolled sheet piling sections to DIN EN 10248-1

Steel grade	Tensile strength N/mm ²	Minimum yield strength N/mm ²	Minimum elongation %
S 270 GP	410	270	24
S 355 GP	480	355	22
S 390 GP	490	390	20
S 430 GP	510	430	19

Steel grades for cold-rolled trench sheeting and lightweight sections to DIN EN 10249-1

Steel grade	Tensile strength N/mm ²	Minimum yield strength N/mm ²	Minimum elongation %
S 275 JR	410	275	22

Standardized steels for combined sheet piling

Steel grade	Standard
General structural steels	EN 10025
Fine-grain structural steels	EN 10113
Weathering steels	EN 10155
Steels for sheet piling	EN 10248
Special steels, PT series	PT material standard Special works steels with minimum yield strengths of 355 to 460 N/mm ²
Further steels on request	e.g. BS, NF, ASTM, JIS, CSAG, GOST, UNI

All section dimensions can be supplied to current national and international standards, also to customer specification if required. A selection can be found in the "steel grades" table.


Interlocks

Corner and junction piles for U- and Z-piles*

Connectors for corners and junctions for sheet piling sections with LARSEN interlock
Interlocks in S 355


Omega 17

Weight: 17.30 kg/m

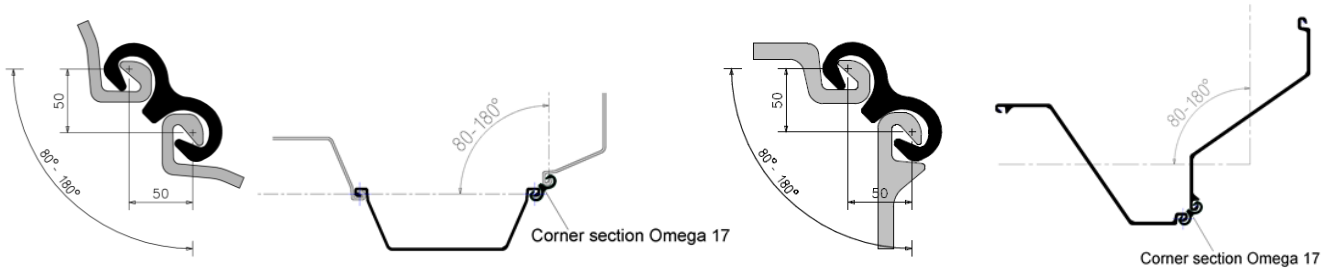


Corner section 20

Weight: 16.50 kg/m

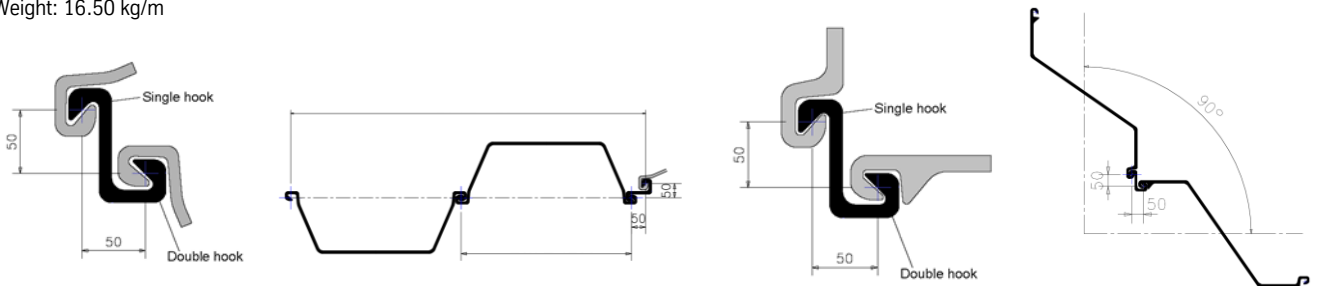


Corner section 22

Weight: 9.20 kg/m

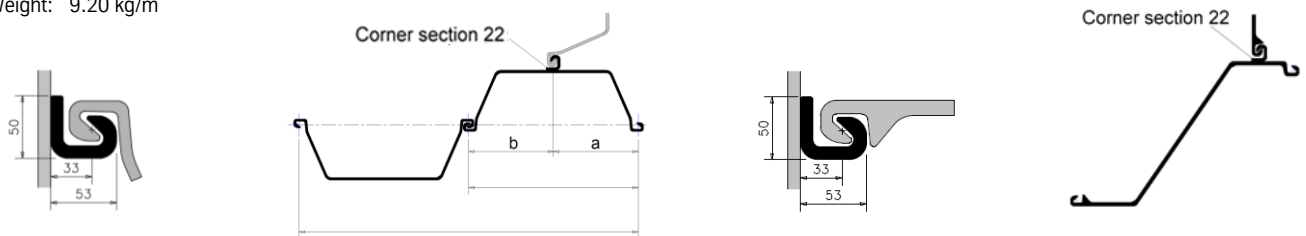

Folded corner pile

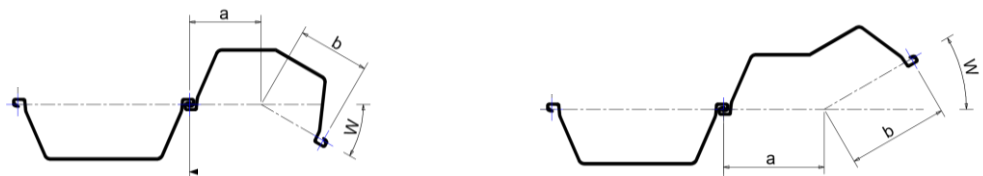



*Corner piles are connected to the sheet piles in accordance with DIN EN 12063 and are not suitable for single driving.

Corner and junction piles for U- and Z-piles*

SteelWall® connectors for U- and Z-piles
Interlocks in S 355



LVO

Weight: 13.85 kg/m

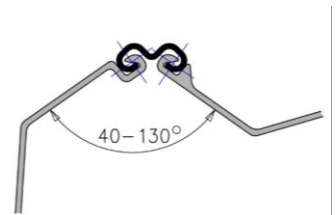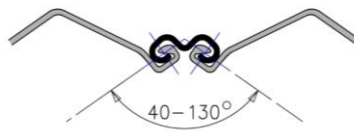




LV20n

Weight: 13.82 kg/m

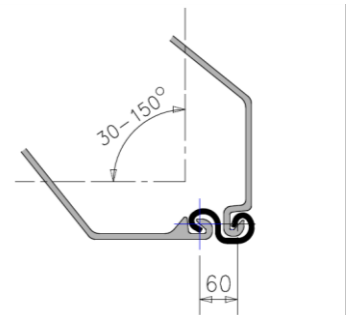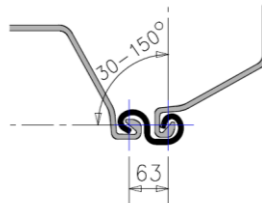

LV22

Weight: 8.0 kg/m




*Corner piles are connected to the sheet piles in accordance with DIN EN 12063 and are not suitable for single driving.
"SteelWall®" is a trademark of SteelWall ISH GmbH, Germany.

Corner and junction piles for U- and Z-piles, traditional*

SteelWall® connectors for U- and Z-piles, traditional
Interlocks in S 355


LOT

Weight: 18.0 kg/m

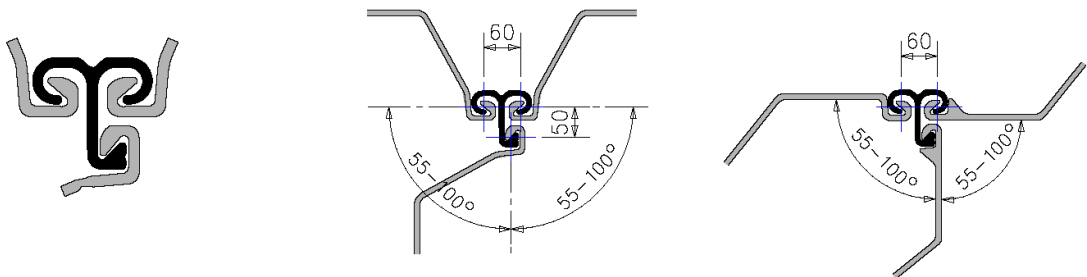


LT

Weight: 17.6 kg/m

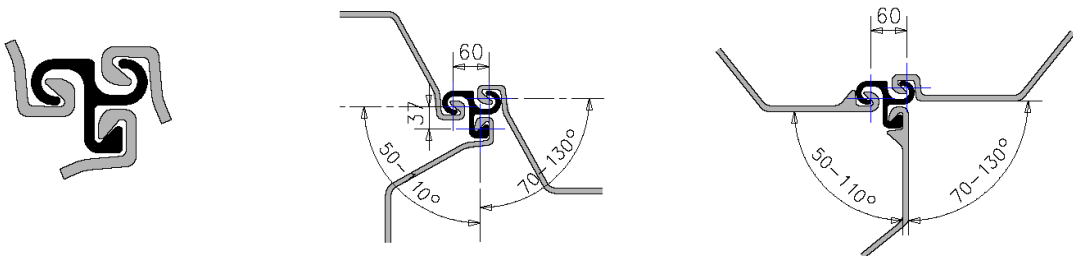

LV-Omega

Weight: 14.0 kg/m

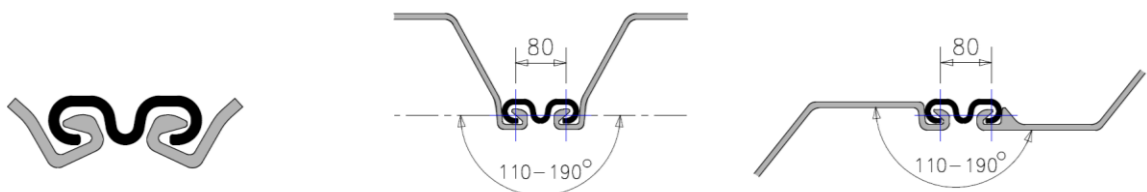



**Corner piles are connected to the sheet piles in accordance with DIN EN 12063 and are not suitable for single driving.
"SteelWall®" is a trademark of SteelWall ISH GmbH, Germany.

Corner and junction piles for U- and Z-piles, universal*

SteelWall® connectors for U- and Z-piles, universal
Interlocks in S 355




LS90

Weight: 12.70 kg/m

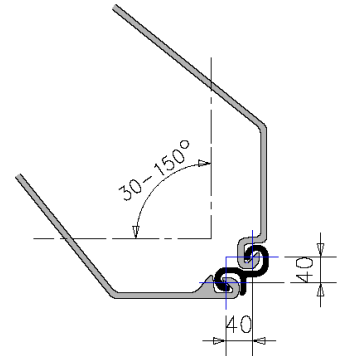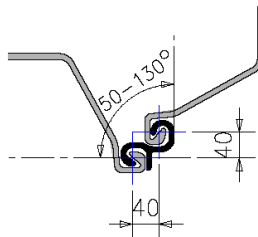



LTO

Weight: 19.80 kg/m

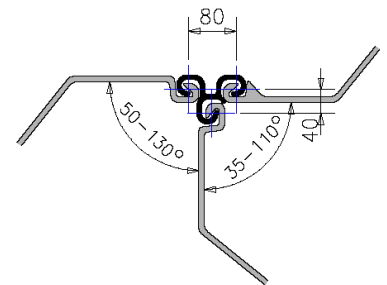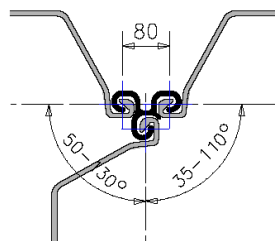



LTS

Weight: 19.00 kg/m

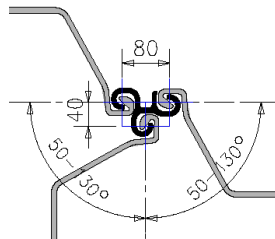

LTZ

Weight: 19.00 kg/m

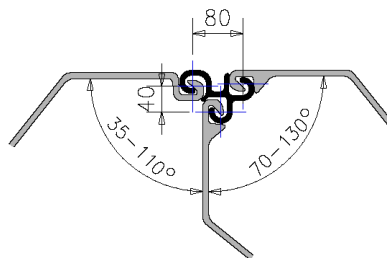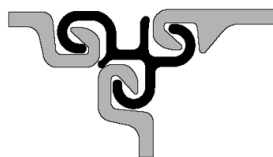


**Corner piles are connected to the sheet piles in accordance with DIN EN 12063 and are not suitable for single driving.
"SteelWall®" is a trademark of SteelWall ISH GmbH, Germany.

Corner and junction piles for cold rolled sheet piles*

SteelWall® connectors for cold rolled sheet piles
Interlocks in S 355



CF 90

Weight: 17.50 kg/m

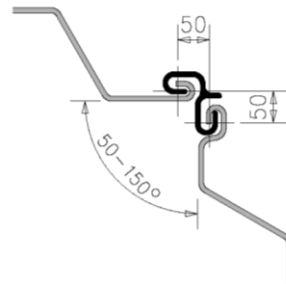



CF-Junction

Weight: 8.90 kg/m



CFT

Weight: 25.80 kg/m

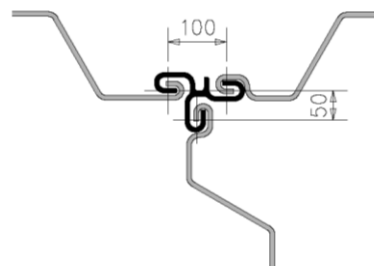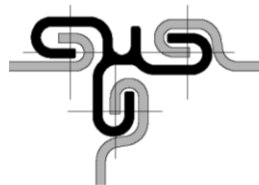

*Corner piles are connected to the sheet piles in accordance with DIN EN 12063 and are not suitable for single driving.
"SteelWall®" is a trademark of SteelWall ISH GmbH, Germany.



Sealing systems thyssenkrupp interlock sealing system

Guiding


When driving sections with sealed interlocks, particular attention must be paid to guiding to ensure the piles do not lean to the front, rear or side. Any corrective measures applied must not cause any narrowing of any interlock slots containing profiled seals. DIN EN 12063 and EAU 2020 contain useful advice.

Driving direction

When installing sections with sealed interlocks, the direction of driving must be specified prior to starting work. When pitching double piles on-site, make sure that the free interlock is driven first and the interlock with the seal is threaded into this. For threading, the pile must be turned so that the unsealed interlock points in the direction of driving. The side with the sealant is to be indicated by a colored dot at the top of the pile. Sheet piling should normally be driven continuously. However, staggered installation is also possible. The method used should be chosen on the basis of the overall driving conditions.

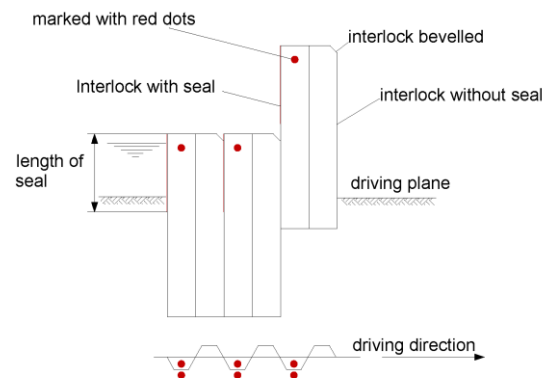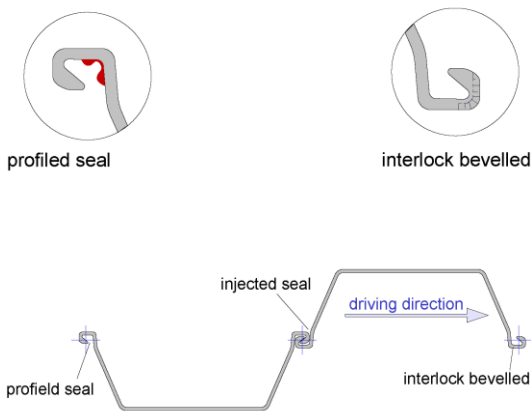

U-Section



Interlock with profiled seal




Middle interlock with injected seal



Z-Section



Interlock with profiled seal




Interlock with profiled seal



Middle interlock with injected seal



Lightweight sections



Interlock with profiled seal



Factory-threaded interlock with seal




Bitumen-based interlock fillers

Material properties


Bituminous-based seals are an elastomeric bitumen hot-poured sealant. After application and cooling, this material may be anything from soft to stiff depending on the ambient temperature. It adheres well to the steel surface.

Direction of driving


The direction of driving must be specified prior to installation when filled interlocks are involved. For threading, the pile must be turned so that the filled interlock points in the direction of driving.

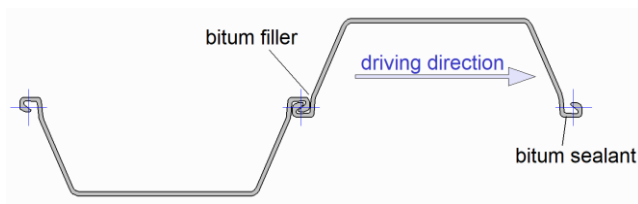

Interlock with bitumen

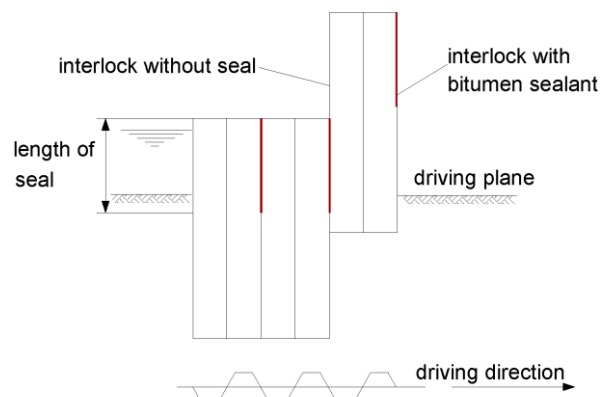

U-Section




Interlock with bitumen sealant



Middle interlock with bitumen sealant



Z-Section




Interlock with bitumen sealant



Middle interlock with bitumen sealant



Lightweight section



Interlock with bitumen sealant



Other sealing methods and installation advice.

Other sealing and installation methods may be necessary depending on the requirements of the particular project. It is therefore essential to investigate and establish the methods to be used in advance.

The following additional sealing methods are available for interlocks that must be sealed after driving:

Where sealing requirements are not excessive, interlocks can be sealed subsequently, e.g. with timber wedges (swelling effect), rubber, or plastic cords.

If absolute watertightness is required, welding the interlocks is the only solution. As a rule, this concerns the threading interlocks only because factory-threaded interlocks can be welded prior to driving. It is important to note that the interlock can only be welded when the surfaces are dry and clean. The weld must be applied to the side of the sheet piling that faces the base of the structure to be erected. Open interlocks can be covered with, for instance, steel flats or steel sections attached to the sheet piling with fillet welds.

Effect of high temperatures

Welding carried out near seals or fillers can be expected to have an adverse, local effect on these materials. If subsequent welding cannot be avoided, resealing will be necessary.

Criteria for selecting a suitable interlock sealing system.

Which interlock seal is suitable for which project? This question has to be considered for every new project, and the answer depends on the project specification and the boundary conditions. We can provide you with the information you need so that you can specify “your” system spot-on.

Example: vertical wall 10.5 m deep is required to encapsulate contaminated site. Investigations have revealed that the soil is contaminated with the following hazardous substances: chlorinated dioxins and furans, chlorobenzenes, chlorophenols, oils, mineral oils, polycyclic aromatic hydrocarbons, aliphatic and aromatic solvents.

From this it follows that the wall required must be resistant to all of the aforementioned substances. The permeability required is $k \leq 1,0 \cdot 10^{-9}$ m/s for a notional thickness of $d = 60$ cm. In light of the quality requirements, only factory-sealed sheet piles are permissible. The section modulus required is $W_y \geq 1,100$ cm³/m. A suitable sealing system can now be determined based on the following parameters:

Permeability criteria

The interlock seepage resistance $\rho \leq k \cdot b/d$

The result is that to achieve the equivalent of a 60 cm thick diaphragm wall with $k \leq 1,0 \cdot 10^{-9}$ m/s the minimum requirement is single piles with a thyssenkrupp interlock sealing system in the threading interlock (critical pile width ≥ 0.50 m).

Spot-on selection.

The following calculation models are based on DIN EN 12063:

Seepage resistance

ρ (m/s)

$$\rho = \frac{q(z) \cdot \gamma}{\Delta p(z)}$$

Seepage rate Q (m³/s · interlock)

The seepage rate Q through a lock can be calculated by:

$$Q = \int_0^{\Delta h+h} q(z) \cdot dz = (\rho/\gamma) \cdot \int_0^{\Delta h+h} \Delta p(z) \cdot dz$$

$$Q = \rho \cdot \Delta h \cdot (0,5 \cdot \Delta h + h)$$

To compare the imperviousness with that of a diaphragm wall, the permeability coefficient k to DIN 18130 Part 1 for soils (porous media) can be taken into account:

$$k = \frac{Q}{i \cdot A} \rightarrow Q = \frac{k \cdot \Delta p(z)}{\gamma \cdot d} \cdot A$$


Considering these fundamental relationships and the number of critical interlocks per m² of wall area results in this relationship for a constant seepage rate Q:

$$\frac{k \cdot \Delta p(z)}{\gamma \cdot d} = \frac{\rho \cdot \Delta p(z)}{\gamma \cdot b}$$

$$\rightarrow \frac{k}{d} = \frac{\rho}{b}$$

where:

- $q(z)$ = discharge rate over time related to interlock length (m³/m · s)
- γ = specific gravity of fluid (kN/m³)
- $\Delta p(z)$ = hydrostatic pressure (kN/m²)

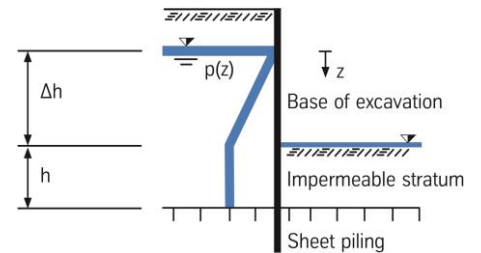

where:

- k = permeability coefficient (m/s)
- Q = measured flow rate (m³/s)
- i = hydraulic gradient (-)
- A = cross-sectional area, wall area (m²)

where:

- d = thickness of diaphragm wall (m)
- b = critical element width for designing seepage rate (m)

The sections given in the table below can be used:

Sections	Critical element width m	Comparable k-value for 60 cm thick diaphragm wall m/s	Leakage requirement satisfied	Imperviousness requirement satisfied
SP (500-series)	0.50	$2.2 \cdot 10^{-10}$	yes	yes
DP (500-series)	1.00	$1.1 \cdot 10^{-10}$	yes	yes
SP (600-series)	0.60	$1.8 \cdot 10^{-10}$	yes	yes
DP (600-series)	1.20	$9.0 \cdot 10^{-11}$	yes	yes

A double pile (600 series) with $W_y \geq 1.100 \text{ cm}^3/\text{m}$ is selected for economic reasons. Its imperviousness therefore compares with that of a 60 cm thick diaphragm wall with a k-value of $9.0 \cdot 10^{-11} \text{ m/s}$, or for an 80 cm thick diaphragm wall a k-value of $1.2 \cdot 10^{-10} \text{ m/s}$. Due to its lower thickness, a slurry wall must exhibit a k-value of $1.2 \cdot 10^{-11}$

m/s in order to achieve the imperviousness of the sheet piling solution.

Resistance criteria

Conventional bituminous interlock fillers are not resistant to pollutants such as aliphatic and aromatic solvents, oils, or mineral oils. However, the thyssenkrupp interlock sealing system has proven to be resistant to these pollutants.


Comparison of k-values

Technical data					
Sealing system	Critical element width b (m)	ρ m/s	k-value required for diaphragm		Slurry wall d = 0.080 m
			d = 0.60 m	d = 0.80 m	
Single piles with bitumen compound in every interlock	0.50	$6.0 \cdot 10^{-8}$	$7.2 \cdot 10^{-8}$	$9.6 \cdot 10^{-8}$	$9.6 \cdot 10^{-9}$
	0.60		$6.0 \cdot 10^{-8}$	$8.0 \cdot 10^{-8}$	$8.0 \cdot 10^{-9}$
Double piles with bitumen compound in driving interlock and poured compound in middle interlock	1.00	$6.0 \cdot 10^{-8}$	$3.6 \cdot 10^{-8}$	$4.8 \cdot 10^{-8}$	$4.8 \cdot 10^{-9}$
	1.20		$3.0 \cdot 10^{-8}$	$4.0 \cdot 10^{-8}$	$4.0 \cdot 10^{-9}$
Single piles with thyssenkrupp interlock sealing system in every interlock	0.50	$1.8 \cdot 10^{-10}$	$2.2 \cdot 10^{-10}$	$2.9 \cdot 10^{-10}$	$2.9 \cdot 10^{-11}$
	0.60		$1.8 \cdot 10^{-10}$	$2.4 \cdot 10^{-10}$	$2.4 \cdot 10^{-11}$
Double piles with thyssenkrupp interlock sealing system in threading interlock and injected sealant in middle interlock	1.00	$1.8 \cdot 10^{-10}$	$1.1 \cdot 10^{-10}$	$1.4 \cdot 10^{-10}$	$1.4 \cdot 10^{-11}$
	1.20		$9.0 \cdot 10^{-10}$	$1.2 \cdot 10^{-10}$	$1.2 \cdot 10^{-11}$
Triple piles with thyssenkrupp thyssenkrupp interlock sealing system in the threading interlock and injected sealant in the middle interlocks	1.50	$1.8 \cdot 10^{-10}$	$7.2 \cdot 10^{-11}$	$9.6 \cdot 10^{-11}$	$9.6 \cdot 10^{-12}$
	1.80		$6.0 \cdot 10^{-11}$	$8.0 \cdot 10^{-11}$	$8.0 \cdot 10^{-12}$

Technical data						
	ρ m/s	Critical element width for double pile m	No. of interlocks with possibly limited seepage	Ingress into excavation		Reduction in quantity of water to be pumped %
				l/s	%	
Groundwater lowering with steel sheet pile wall				~ 115	100	+
Sheet piling without interlock sealing	$8.0 \cdot 10^{-4} \times k_{\text{soil}}/b$	0.5	900	~ 41	36	64
Sheet piling with site-applied bitumen compound in every interlock	$6.0 \cdot 10^{-8}$	0.5	900	~ 3.1	3	97
Sheet piling with factory-applied bitumen compound in driving interlock and poured compound in middle interlock	$6.0 \cdot 10^{-8}$	1	450	~ 1.5	1.3	99
Sheet piling with thyssenkrupp interlock sealing system in threading interlock and injected sealant in middle interlock	$1.8 \cdot 10^{-10}$	1	450	~ 0.005	0.004	99.9

Anchor equipment Round steel tie rods


Round steel tie rod components and connecting elements

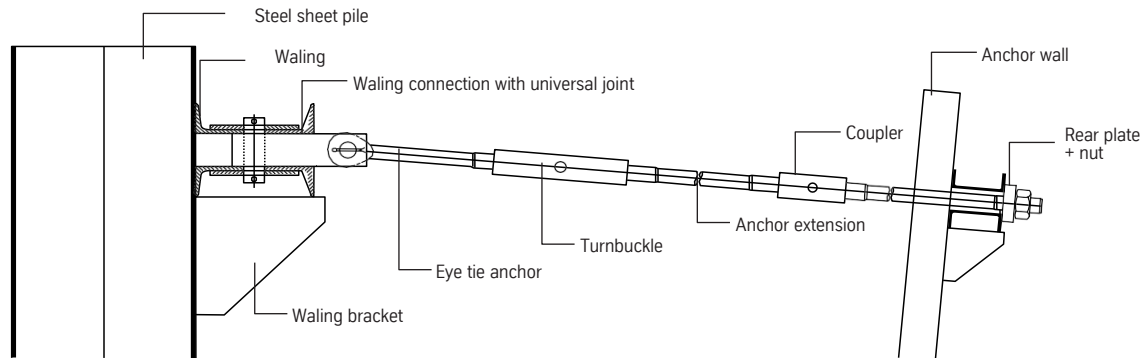

Anchor with upset ends – rolled thread

Round steel tie rods acc. to EAU 2012

Technical data															
Anchor force according to EAU 2012 - $k_t = 0.55$		M 39	M 42	M 45	M 48	M 52	M 56	M 60	M 64	M 68	M 72	M 76	M 80	M 85	M 90
Nominal diameter	D mm	39	42	45	48	52	56	60	64	68	72	76	80	85	90
Shaft diameter	d mm	36	39	42	45	38	41	44	47	50	54	57	60	64	68
Tensile stress area Thread	As mm ²	976	1,121	1,306	1,473	1,758	2,030	2,362	2,676	3,055	3,460	3,889	4,344	4,948	5,591
Cross sectional area Shaft	Ag mm ²	1,017	1,194	1,385	1,590	1,134	1,320	1,521	1,735	1,963	2,290	2,552	2,827	3,217	3,632
ASF 355 Permissible design resistance	Rd kN	205	235	275	309	366	426	491	560	634	736	824	912	1,038	1,172
ASF 460 Permissible design resistance	Rd kN	257	294	345	387	465	537	627	709	813	924	1,042	1,167	1,333	1,510
ASF 500 Permissible design resistance	Rd kN	273	313	366	412	494	570	666	754	864	982	1,107	1,240	1,416	1,605
Weight (Shaft)	G kg/m	7.99	9.38	10.88	12.49	8.90	10.36	11.94	13.62	15.41	17.98	20.03	22.20	25.25	28.51

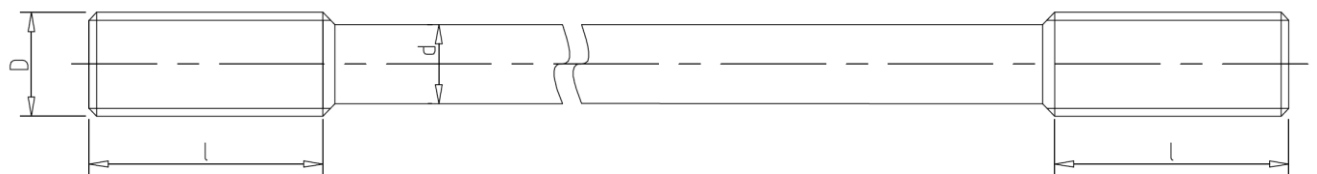


Technical data															
Anchor force according to EAU 2012 - $k_t = 0.55$		M 95	M 100	M 105	M 110	M 115	M 120	M 125	M 130	M 135	M 140	M 145	M 150	M 155	M 160
Nominal diameter	D mm	95	100	105	110	115	120	125	130	135	140	145	150	155	160
Shaft diameter	d mm	73	77	81	85	89	93	97	101	105	109	113	118	123	127
Tensile stress area Thread	As mm ²	6,273	6,995	7,755	8,556	9,395	10,274	11,191	12,149	13,145	14,181	15,256	16,370	17,524	18,716
Cross sectional area Shaft	Ag mm ²	4,185	4,657	5,153	5,675	6,221	6,793	7,390	8,012	8,659	9,331	10,029	10,936	11,882	12,668
ASF 355 Permissible design resistance	Rd kN	1,351	1,503	1,663	1,831	2,008	2,192	2,385	2,586	2,795	3,011	3,237	3,529	3,835	4,088
ASF 460 Permissible design resistance	Rd kN	1,699	1,898	2,108	2,330	2,562	2,806	3,061	3,326	3,603	3,891	4,190	4,500	4,821	5,153
ASF 500 Permissible design resistance	Rd kN	1,805	2,017	2,240	2,476	2,723	2,981	3,252	3,534	3,828	4,134	4,452	4,781	5,122	5,475
Weight (Shaft)	G kg/m	32.86	36.56	40.45	44.55	48.84	53.32	58.01	62.89	67.94	73.25	78.73	85.85	93.28	99.44

Anchor with upset ends – rolled thread

Round steel tie rods acc. to DIN EN 1993-5


Technical data															
Anchor force according to DIN EN 1993-5 - $k_t = 0.60$															
Nominal diameter	D mm	M 39	M 42	M 45	M 48	M 52	M 56	M 60	M 64	M 68	M 72	M 76	M 80	M 85	M 90
Shaft diameter	d mm	36	39	42	45	38	41	44	47	50	54	57	60	64	68
Tensile stress area Thread	As mm ²	976	1,121	1,306	1,473	1,758	2,030	2,362	2,676	3,055	3,460	3,889	4,344	4,948	5,591
Cross sectional area Shaft	Ag mm ²	1,017	1,194	1,385	1,590	1,134	1,320	1,521	1,735	1,963	2,290	2,552	2,827	3,217	3,632
ASF 355 Permissible design resistance	Rd kN	239	274	320	361	403	469	540	616	697	813	906	1,004	1,142	1,289
ASF 460 Permissible design resistance	Rd kN	300	344	401	453	522	607	699	798	903	1,054	1,174	1,301	1,480	1,671
ASF 500 Permissible design resistance	Rd kN	318	366	426	481	567	660	760	867	982	1,129	1,269	1,414	1,608	1,816
ASF 720 Permissible design resistance	Rd kN	422	484	564	636	759	877	1,020	1,156	1,320	1,495	1,680	1,877	2,138	2,415
Weight (Shaft)	G kg/m	7.99	9.38	10.88	12.49	8.90	10.36	11.94	13.62	15.41	17.98	20.03	22.20	25.25	28.51

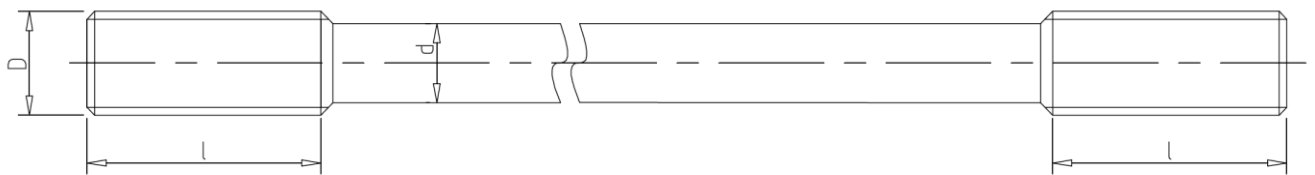

Technical data															
Anchor force according to DIN EN 1993-5 - $k_t = 0.60$															
Nominal diameter	D mm	M 95	M 100	M 105	M 110	M 115	M 120	M 125	M 130	M 135	M 140	M 145	M 150	M 155	M 160
Shaft diameter	d mm	73	77	81	85	89	93	97	100	105	110	115	120	125	130
Tensile stress area Thread	As mm ²	6,273	6,995	7,755	8,556	9,395	10,274	11,191	12,149	13,145	14,181	15,256	16,370	17,524	18,716
Cross sectional area Shaft	Ag mm ²	4,185	4,657	5,153	5,675	6,221	6,793	7,390	7,854	8,659	9,503	10,387	11,310	12,272	13,273
ASF 355 Permissible design resistance	Rd kN	1,486	1,653	1,829	2,014	2,209	2,411	2,623	2,788	3,074	3,374	3,687	4,007	4,290	4,582
ASF 460 Permissible design resistance	Rd kN	1,925	2,142	2,370	2,610	2,862	3,125	3,399	3,613	3,983	4,356	4,687	5,029	5,383	5,750
ASF 500 Permissible design resistance	Rd kN	2,048	2,283	2,531	2,793	3,067	3,353	3,653	3,927	4,291	4,629	4,979	5,343	5,720	6,109
ASF 720 Permissible design resistance	Rd kN	2,710	3,022	3,350	3,696	4,059	4,438	4,835	5,248	5,679	6,126	6,591	7,072	7,570	8,085
Weight (Shaft)	G kg/m	32.86	36.56	40.45	44.55	48.84	53.32	58.01	61.65	67.94	74.60	81.50	88.78	96.29	104.00

Anchor with rolled thread

Technical data															
Anchor force according to DIN EN 1993-5 - $k_t = 0.90$															
Nominal diameter	D mm	M 39	M 42	M 45	M 48	M 52	M 56	M 60	M 64	M 68	M 72	M 76	M 80	M 85	M 90
Shaft diameter	d mm	36	39	42	45	49	52	56	60	64	68	72	76	81	86
Tensile stress area Thread	As mm ²	976	1,121	1,306	1,473	1,758	2,030	2,362	2,676	3,055	3,460	3,889	4,344	4,948	5,591
Cross sectional area Shaft	Ag mm ²	1,017	1,194	1,385	1,590	1,847	2,124	2,463	2,827	3,217	3,632	4,072	4,536	5,153	5,809
ASF 355	Rd kN	346	398	464	523	624	721	839	950	1,085	1,228	1,381	1,542	1,757	1,985
ASF 460	Rd kN	449	516	601	678	809	934	1,087	1,231	1,405	1,592	1,789	1,998	2,276	2,572
ASF 500	Rd kN	478	549	639	721	861	994	1,156	1,310	1,496	1,694	1,904	2,127	2,423	2,737
ASF 720	Rd kN	632	726	846	955	1,139	1,315	1,531	1,734	1,980	2,242	2,520	2,815	3,206	3,623
Weight (Shaft)	G kg/m	7.99	9.38	10.88	12.49	14.80	16.62	19.34	22.20	25.25	28.51	31.96	35.61	40.45	45.60

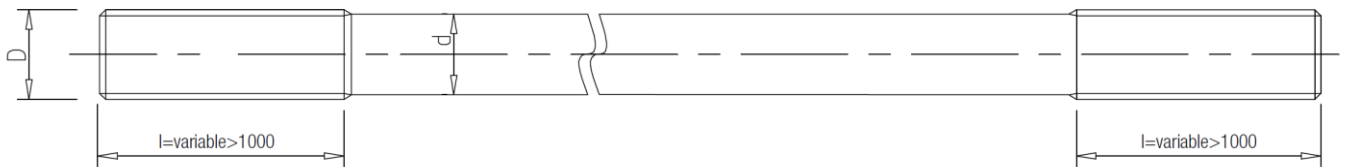

Technical data															
Anchor force according to DIN EN 1993-5 - $k_t = 0.90$															
Nominal diameter	D mm	M 95	M 100	M 105	M 110	M 115	M 120	M 125	M 130	M 135	M 140	M 145	M 150	M 155	M 160
Shaft diameter	d mm	91	96	101	106	111	116	121	126	131	136	141	146	151	156
Tensile stress area Thread	As mm ²	6,273	6,995	7,755	8,556	9,395	10,274	11,191	12,149	13,145	14,181	15,256	16,370	17,524	18,716
Cross sectional area Shaft	Ag mm ²	6,504	7,238	8,012	8,825	9,677	10,568	11,499	12,469	13,478	14,527	15,615	16,742	17,908	19,113
ASF 355	Rd kN	2,227	2,483	2,753	3,037	3,335	3,647	3,973	4,313	4,666	5,034	5,416	5,811	6,221	6,644
ASF 460	Rd kN	2,886	3,218	3,567	3,936	4,322	4,726	5,148	5,589	6,047	6,523	7,018	7,530	8,061	8,609
ASF 500	Rd kN	3,071	3,425	3,797	4,189	4,600	5,030	5,479	5,948	6,436	6,943	7,469	8,015	8,580	9,163
ASF 720	Rd kN	4,065	4,533	5,025	5,544	6,088	6,658	7,252	7,873	8,518	9,189	9,886	10,608	11,356	12,128
Weight (Shaft)	G kg/m	51.06	56.82	62.89	69.27	75.96	82.96	90.27	97.88	105.80	114.04	122.57	131.42	140.58	150.00

Permissible design resistances R_d according to DIN 1993-5 (D) / Stressed area

Round steel tie rods and bolts

(The threads - Metric thread - are rolled up)

The design resistances are calculated using the following equation over the minimum cross section:

$$F_{t9,Rd} = (\text{Shaft cross section}) \quad A_g \times f_{y,k} / \gamma_{M0} \quad \text{where } \gamma_{M0} = 1.00$$

$$F_{t,Rd} = (\text{Thread cross section}) \quad k_t \times A_s \times f_{ub,k} / \gamma_{M2} \quad \text{where } \gamma_{M2} = 1.25$$

Verification for the ultimate limit state to DIN EN 1993-5:

$$Z_d < R_d$$

$$Z_d: \quad \text{design value of anchor force } Z_d = Z_{G,k} * \gamma_G + Z_{Q,k} * \gamma_Q$$

$$R_d: \quad \text{design resistance of anchor } R_d = \text{Min} [F_{t9,Rd} ; F_{t,Rd}]$$

A_g : cross-sectional area in shaft zone

A_s : tensile stress area in threaded zone

$f_{y,k}$: yield stress

$f_{ub,k}$: tensile strength

γ_{M0} : partial safety factor to DIN EN 1993-5 for anchor shaft


γ_{M2} : partial safety factor to DIN EN 1993-5 for threaded area

k_t : notch factor to DIN 1993-5 ($k_t = 0.60$ or 0.90)

Eye anchor

Technical data															
ASF 355 anchor force acc. to DIN EN 1993-5 with $k_t = 0.6$		A150	A175	A200	A200	A225	A225	A225	A250	A275	A300A	A300B	A325	A350	A375A
Shaft diameter	d mm	36	39	42	42	45	45	45	48	52	56	60	64	68	72
Thickness eye	c mm	25	30	33	33	39	39	39	42	47	50	50	55	60	63
Length eye	La mm	86	106	127	127	135	135	135	147	166	190	190	210	220	235
Width eye	a mm	72	85	105	105	110	110	110	125	135	155	155	165	180	190
Bolt diameter	d0 mm	30	33	36	36	40	40	40	47	52	56	56	62	68	70

Technical data															
ASF 355 anchor force acc. to DIN EN 1993-5 with $k_t = 0.6$		A375B	A400	A425	A450	A450	A475	A500	A525	A550	A575	A575	A600	A625	A650
Shaft diameter	d mm	75	80	85	90	90	95	100	105	110	115	115	120	125	130
Thickness eye	c mm	63	66	72	75	75	80	85	90	95	100	100	105	115	120
Length eye	La mm	235	253	290	300	300	323	340	350	365	373	373	380	439	459
Width eye	a mm	190	210	230	240	240	255	270	275	290	300	300	310	330	340
Bolt diameter	d0 mm	70	76	80	85	85	90	95	100	100	105	105	110	115	120

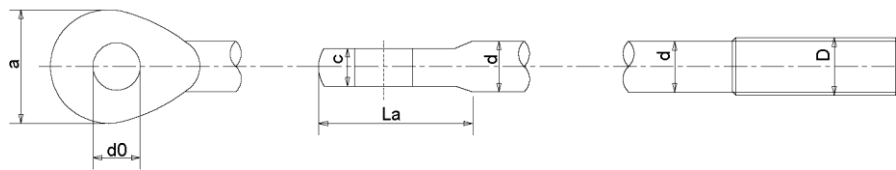


Technical data															
ASF 500 anchor force acc. to DIN EN 1993-5 with $k_t = 0.6$		A150	A175	A200	A200	A225	A225	A225	A250	A275	A300A	A300B	A325	A350	A375A
Shaft diameter	d mm	36	39	42	42	45	45	45	48	52	56	60	64	68	72
Thickness eye	c mm	25	30	33	33	39	39	39	42	47	50	50	55	60	63
Length eye	La mm	86	106	127	127	135	135	135	147	166	190	190	210	220	235
Width eye	a mm	72	85	105	105	110	110	110	125	135	155	155	165	180	190
Bolt diameter	d0 mm	30	33	36	36	41	41	41	47	52	56	56	62	68	70

Technical data															
ASF 500 anchor force acc. to DIN EN 1993-5 with $k_t = 0.6$		A375B	A400	A425	A450	A450	A475	A500	A525	A550	A575	A575	A600	A625	A650
Shaft diameter	d mm	75	80	85	90	90	95	100	105	110	115	115	120	125	130
Thickness eye	c mm	63	66	72	75	75	80	85	90	95	100	100	105	115	120
Length eye	La mm	235	253	290	300	300	323	340	350	365	373	373	380	439	459
Width eye	a mm	190	210	230	240	240	255	270	275	290	300	300	310	330	340
Bolt diameter	d0 mm	70	76	80	85	85	90	95	100	105	110	110	115	120	125

Technical data															
ASF 720 anchor force acc. to DIN EN 1993-5 with $k_t = 0.6$		A150	A175	A200	A200	A225	A225	A225	A250	A275	A300A	A300B	A325	A350	A375A
Shaft diameter	d mm	36	39	42	42	45	45	45	48	52	56	60	64	68	72
Thickness eye	c mm	25	30	33	33	39	39	39	42	47	50	50	55	60	63
Length eye	La mm	86	106	127	127	135	135	135	147	166	190	190	210	220	235
Width eye	a mm	72	85	105	105	110	110	110	125	135	155	155	165	180	190
Bolt diameter	d0 mm	30	33	40	40	44	44	44	50	55	61	61	66	72	76

Technical data															
ASF 720 anchor force acc. to DIN EN 1993-5 with $k_t = 0.6$		A375B	A400	A425	A450	A450	A475	A500	A525	A550	A575	A575	A600	A625	A650
Shaft diameter	d mm	75	80	85	90	90	95	100	105	110	115	115	120	125	130
Thickness eye	c mm	63	66	72	75	75	80	85	90	95	100	100	105	115	120
Length eye	La mm	235	253	290	300	300	323	340	350	365	373	373	380	439	459
Width eye	a mm	190	210	230	240	240	255	270	275	290	300	300	310	330	340
Bolt diameter	d0 mm	76	85	90	95	95	100	105	110	110	115	115	125	130	135

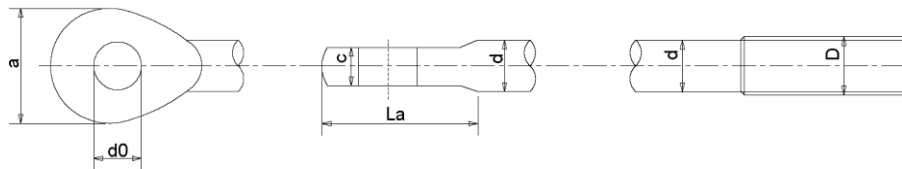

thyssenkrupp drilled injection pile

Basic information

The thyssenkrupp ASF drilled injection pile according to approval Z-34.14-243 is a micropile system according to DIN 14199 and DIN SPEC 18539. A main feature of the thyssenkrupp ASF drilled injection pile is the use of a good-tolerance steel grade. As a result, the system has low steel elongation under load and higher load-bearing reserves than comparable micropile systems. Currently, micropiles with a length of up to 34 meters can be supplied in one piece.

Corrosion protection

Permanent corrosion protection is ensured with the help of the cement stone covering of the grout body. The use of an additional grouted corrugated sheathing, as in comparable systems, is not necessary. The permanent corrosion protection of the pile head is achieved either by placing the pile head in concrete or by using the pile head construction in accordance with the approval.

Intended purpose

Micropile for tie-back anchoring

According to DIN EN 14199 for load transfer of tensile loads into deeper, load-bearing soil layers

Micropile for foundations

According to DIN EN 14199 for load transfer of compressive and tensile loads in deeper, load-bearing soil layers

Technical data ASF 500/700

Nominal size	Inches		3	3½	4	4¼
Outer diameter	Ø	mm	71.0	83.0	96.0	102.0
Cross-sectional area	A	cm ²	37.0	51.3	67.7	77.3
Yield strength/tensile strength	$f_{y/t}$	N/mm ²	500/700	500/700	500/700	500/700
Characteristic load-bearing capacity for tensile load ¹⁾	R_k	kN	2,036	2,598	3,385	4,139
Characteristic load-bearing capacity under compressive load ¹⁾	R_k	kN	2,127	2,598	3,385	4,242
Elongation stiffness	E · A	MN	611	912	1,365	1,650
Weight		kg/m	31.1	42.5	56.8	64.1

1) Utilization of the load-bearing capacity is dependent on the cement stone cover according to approval Z-34.14-243

2) The use of the thyssenkrupp ASF drilled injection piles are regulated in Germany by National Technical Approval Z-34.14-243 issued by the German Institute for Civil Engineering (DIBt)

Dimensioning

The verification of the internal and external load-carrying capacity must always be performed out when micropiles are used as a tie-back anchorage or as an foundation pile. Further verifications such as the buckling analysis and the serviceability analysis may be required depending on the intended use.

Verification of the load-carrying capacity of the pile materials

The verification of the load-carrying capacity of the pile material proves that the design value of actions E_d is less than the design value of the pile resistance .

The verification of the load-carrying capacity of the pile materials is carried out as follows:

Design value of actions (E_d) ≤ design value of pile resistance (R_d)

where:

$$E_d = \gamma_G * G_k + \gamma_Q * Q_k$$

$$R_d = R_k / \gamma_M$$

with

- E_d Design value of actions
- γ_G Partial safety factor for permanent actions
= 1.35 for BS-P (constant situation)
= 1.20 for BS-T (temporary situation)
- γ_Q Partial safety factor for variable actions
= 1.50 for BS-P (constant situation)
= 1.30 for BS-T (temporary situation)
- R_d Design value of the pile resistance
- R_k Characteristic load capacity
- γ_M Partial safety factor Material resistance
= 1.15 for BS-P, BS-T und BS-A

Verification of the external load carrying capacity of the grout/soil friction


Micropiles transfer loads to the soil via the skin friction.

For this purpose, it must be ensured that the surface of the grout body is sufficiently large enough. The required surface area is determined by the diameter and length of the grout body and the skin friction value $q_{s,i,k}$ of the soil layer.

With the help of site investigations and pile test, the actually existing skin friction value of the existing soils can be determined.

Alternatively, the design of the external load-carrying capacity can be performed with the empirical values of the skin friction according to EA-Piles Tab. 5.29 und 5.30.


Application example deep foundation

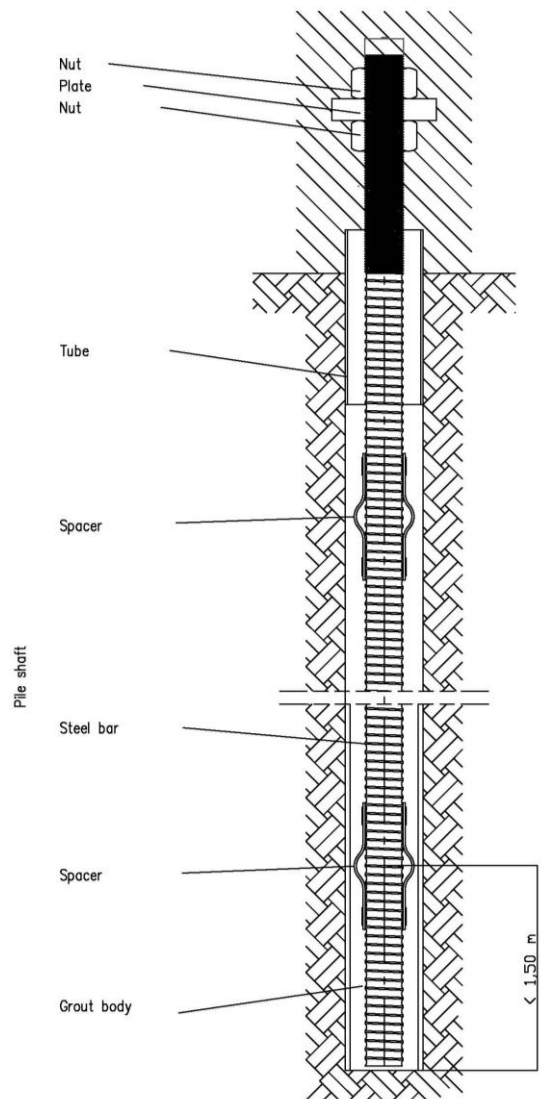

Permanent pile head construction in detail according to Approval Z-34.14-243

In the case of tie-back anchoring of a sheet pile or combination wall, installation of the pile head in concrete is not always wanted or possible. For this reason, a pile head construction was developed for the thyssenkrupp ASF drilled injection pile that allows the permanent use (100+ years).

For the planning of the micropile, the required dimensions of the pile head-construction can be taken from the approval. The additional verification of the plates, the pipe sockets and the weld seams can be omitted. Because of this the planning of the micropiles can be performed more quickly and efficiently.

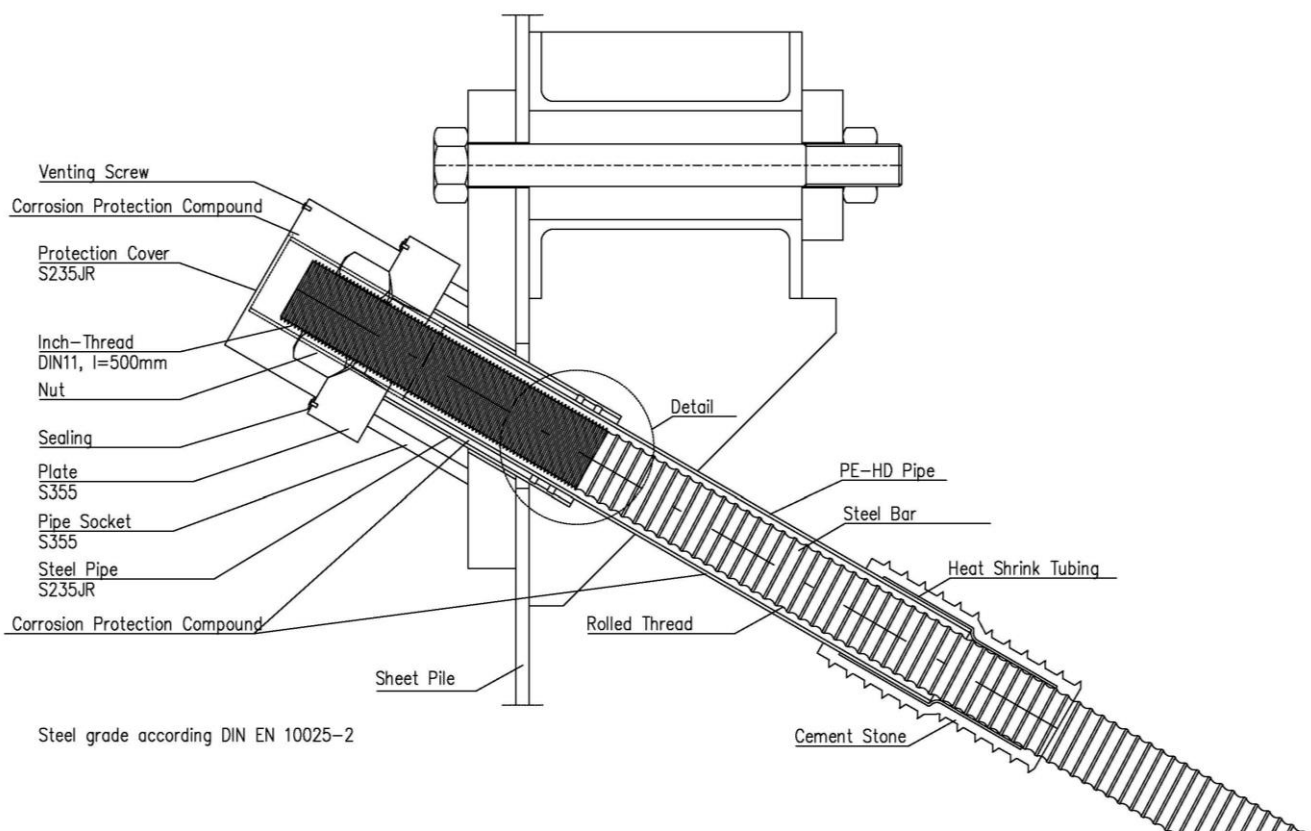

Materials Services Infrastructure

thyssenkrupp Infrastructure GmbH
Hollestraße 7a
45127 Essen, Germany
T: +49 201 844 - 562313
F: +49 201 844 - 562333
steelsections.tkinfrastructure@
thyssenkrupp.com
www.thyssenkrupp-infrastructure.com

Australia, New Zealand
thyssenkrupp Infrastructure Ltd.
Level 5, Tower B 799 Pacific Highway
Chatswood NSW 2067, Australia
P: +61 2 8448-3555
F: +61 2 9411-4311
www.thyssenkrupp-infrastructure.com.au

Baltic States
UAB thyssenkrupp Baltija
Liepų str.83,
Klaipėda 92195, Lithuania
P: +370 46 355-401
F: +370 46 355-032
<https://www.thyssenkrupp-infrastructure.ru>

Russian Federation
OOO thyssenkrupp Infrastructure
Prospekt Bolshevikov 54 B, office 211
193315 St.-Petersburg
Russian Federation
P: +7 812 337-6510
F: +7 812 337-6511
russia.tkinfrastructure@thyssenkrupp.com
<https://www.thyssenkrupp-infrastructure.ru>